

United States
Department of
Agriculture

Forest Service




Southeastern Forest
Experiment Station

Research Paper
SE-253

April 1986

Weight, Volume, and Physical Properties of Major Hardwood Species in the Southern Appalachian Mountains

Alexander Clark III and James G. Schroeder

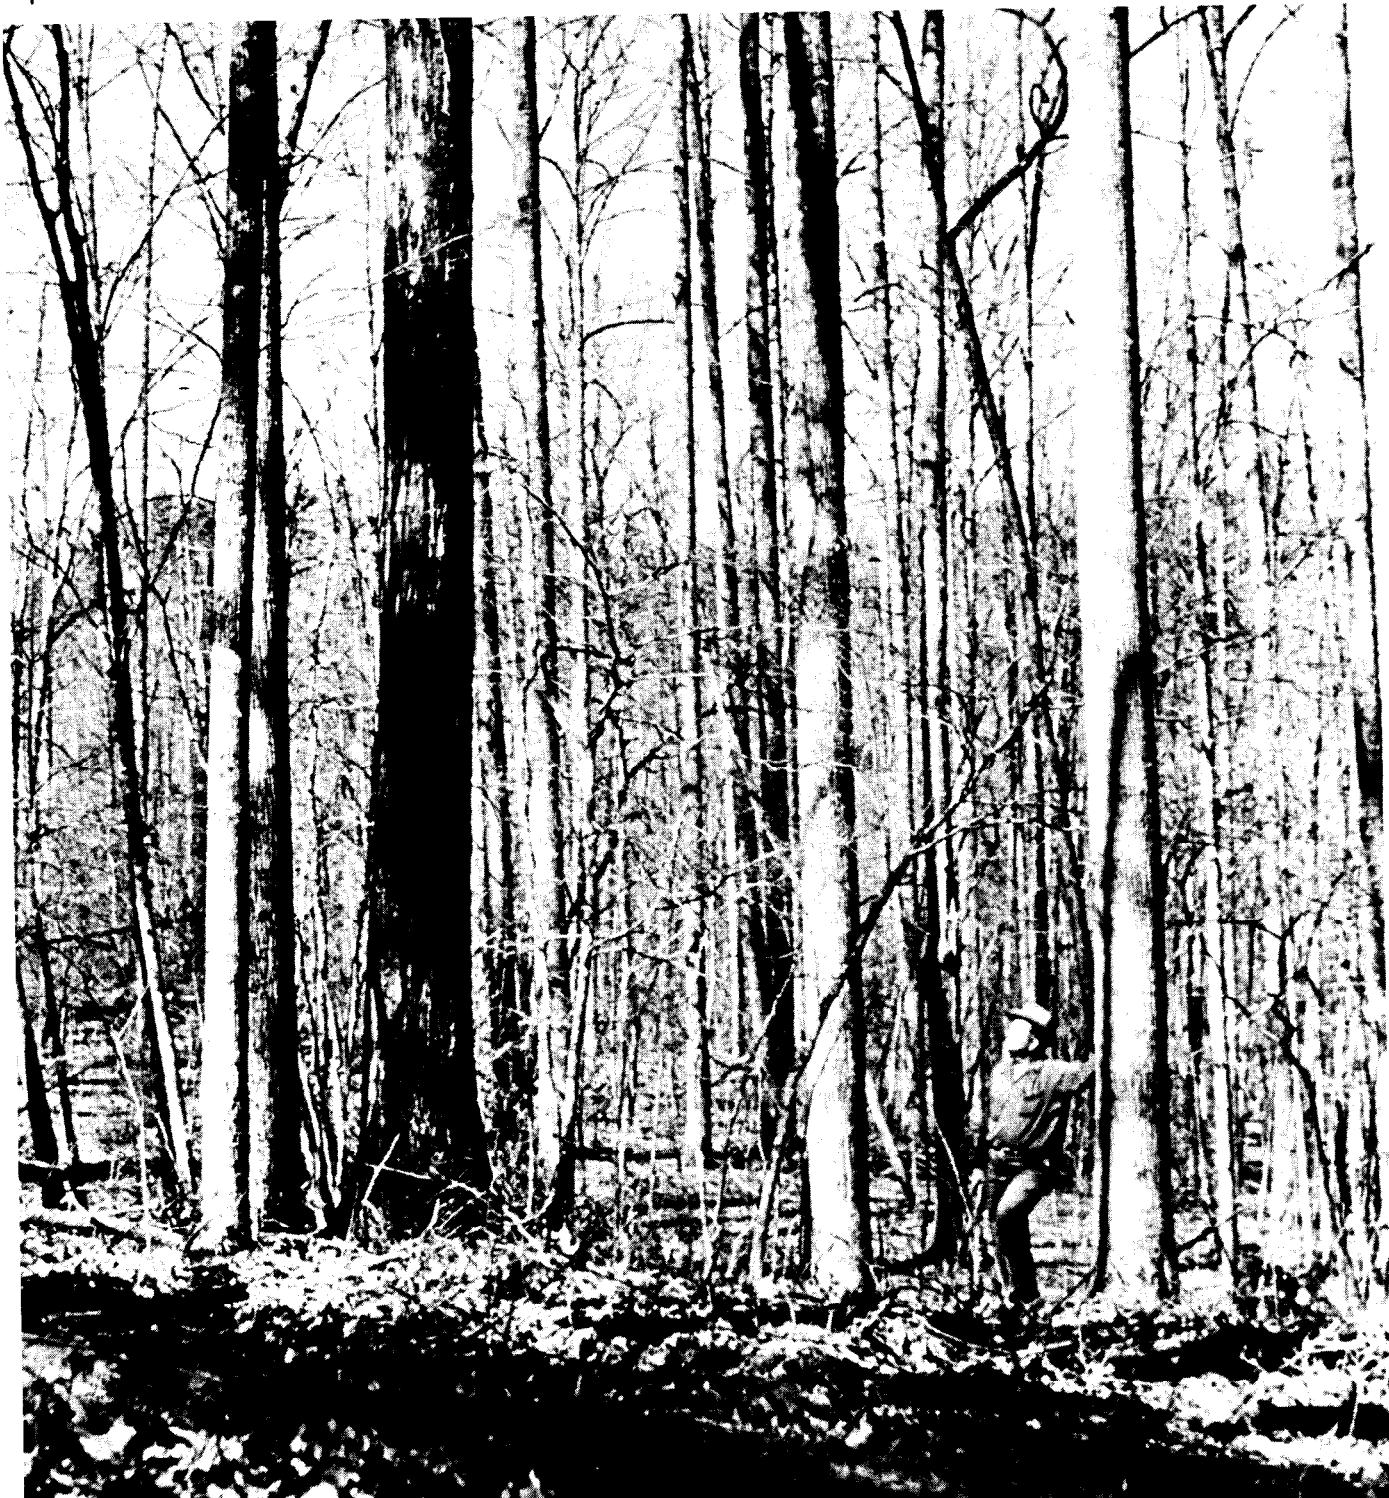

April 1986

**Southeastern Forest Experiment Station
P.O. Box 2680
Asheville, NC 28802**

Weight, Volume, and Physical Properties of Major Hardwood Species in the Southern Appalachian Mountains

Alexander Clark III, Wood Scientist
Athens, Georgia

and

James G. Schroeder, Principal Wood Scientist (retired)

Asheville, North Carolina



Contents

	<u>Page</u>
Procedure	2
Field	2
Laboratory	2
Analysis	3
Results	5
Physical Properties of Sample Trees	5
Prediction Equations	6
How to Use Prediction Equations	7
Literature Cited	10
 Tables (for hardwood species in the Southern Appalachian Mountains)	
1. Mean and range of tree age and measurements, by species and tree size class	13
2. Average specific gravity of wood, bark, and wood and bark combined, by tree-component and size class	16
3. Average moisture content of wood, bark, and wood and bark combined, by tree component and size class	22
4. Average proportion of wood and bark green weight in bark, by tree component and size class	27
5. Average green weight per cubic foot of wood, bark, and wood and bark combined, by tree component and size class	29
6. Average green weight of wood and bark per cubic foot of wood, hytreecomponentandsizeclass	34
7. Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined, and wood alone, with d.b.h. as the independent variable	36
8. Regression equations for estimating green and dry weight of the total-stem wood and bark combined and wood alone, with d.b.h. as the independent variable	38
9. Regression equations for estimating cubic-foot volume of the above-stump total-tree wood and bark combined and wood alone, with d.b.h. as the independent variable	40
10. Regression equations for estimating cubic-foot volume of the total-stem wood and bark combined and wood alone, with d.b.h. as the independent variable	41

11.	<i>Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone, with d.b.h. and total height as the independent variables</i>	42
12.	<i>Regression equations for estimating green and dry weight of the total-stem wood and bark combined and wood alone, with d.b.h. and total height as the independent variables</i>	44
13.	<i>Regression equations for estimating cubic-foot volume of the above-stump total-tree wood and bark combined and wood alone, with d.b.h. and total height as the independent variables</i>	46
14.	<i>Regression equations for estimating cubic-foot volume of the total-stem wood and bark combined and wood alone, with d.b.h. and total height as the independent variables</i>	47
15.	<i>Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone, with d.b.h. and height to a 4-inch top as the independent variables</i>	48
16.	<i>Regression equations for estimating green and dry weight of the total-stem wood and bark combined and wood alone, with d.b.h. and height to a 4-inch top as the independent variables</i>	50
17.	<i>Regression equations for estimating cubic-foot volume of the above-stump total-tree wood and bark combined and wood alone, with d.b.h. and height to a 4-inch top as the independent variables</i>	52
18.	<i>Regression equations for estimating cubic-foot volume of the total-stem wood and bark combined and wood alone, with d.b.h. and height to a 4-inch top as the independent variables</i>	53
19.	<i>Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone, with d.b.h. and saw-log merchantable height as the independent variables</i>	54
20.	<i>Regression equations for estimating green and dry weight of the saw-log merchantable-stem wood and bark combined and wood alone, with d.b.h. and saw-log merchantable height as the independent variables</i>	56
21.	<i>Regression equations for estimating cubic-foot volume of the above-stump total-tree wood and bark combined and wood alone, with d.b.h. and saw-log merchantable height as the independent variables</i>	58
22.	<i>Regression equations for estimating cubic-foot volume of the saw-log merchantable-stem wood and bark combined and wood alone, with d.b.h. and saw-log merchantable height as the independent variables</i>	59

	<u>Page</u>
23. Regression coefficients for estimating above-stump stem weight to a specified d.o.b. top diameter as a proportion of the total-stem weight	60
24. Regression coefficients for estimating above-stump stem volume to a specified d.o.b. top diameter as a proportion of the total-stem volume	61
25. Regression coefficients for estimating stem weight to a specified d.o.b. top diameter as a proportion of the saw-log stem weight	62
26. Regression coefficients for estimating stem volume to a specified d.o.b. top diameter as a proportion of the saw-log stem volume	63

ABSTRACT

The weight, volume, and physical properties of trees 1 to 20 inches d.b.h. were determined for basswood, blackgum (upland), red maple, yellow poplar, white oak, sweet birch, black locust, hickory, black oak, chestnut oak, northern red oak, scarlet oak, and white oak in the Southern Appalachian Mountains. Hard hardwoods, soft hardwoods, and individual species equations are presented for predicting green and dry weight and green volume of the total tree above-stump and its components by using d.b.h. and total height, d.b.h. and height to a 4-inch top, d.b.h. and saw-log merchantable height, and d.b.h. alone. Average specific gravity, moisture content, and weight per cubic foot of wood, bark, and wood an 1 hark combined are presented for each species by tree size class and component. Bark percentage is also presented for each species by tree size class and component.

Keywords: Biomass, equations, specific gravity, moisture content, bark percentage, weight per cubic foot.

The hardwood forests of the Southern -Appalachian Mountains can contribute significantly to supplies of solid wood, fiber, and energy wood through improved utilization and forest management. Few data, however, exist on the weight, volume, and physical properties of the total tree and its components for hardwood species of this region.

To meet this need, the USDA Forest Service collected tree weight and volume data for the important hardwood species growing in this region. These data were used to develop equations for estimating the weight and volume of individual trees and tree components. The specific gravity, moisture content, and bark content of the trees sampled were also determined.

This Paper presents green volume and green and dry weight equations for the total tree and tree components of 13 species-- basswood (Tilia americana L.), upland blackgum (Nyssa sylvatica Marsh.), red maple (Acer rubrum L.), yellow poplar (Liriodendron tulipifera L.), white ash (Fraxinus americana L.), sweet birch (Betula lenta L.), black locust (Robinia pseudoacacia L.), hickory species (Carya spp.), black oak (Quercus velutina Lam.), chestnut oak (Q. prinus L.), northern red oak (Q. rubra L.), scarlet- coccinea Mienchh.), and white oak (Q. alba L.). Equations were developed from tree data collected in the Southern Appalachian Mountains of western North Carolina and northeastern Georgia. These species account for more than 85 percent of the commercial hardwood volume in this region. Equations were also developed for the combined hard hardwoods, combined soft hardwoods, and all 13 species.

Equations are given for estimating the weight and volume of wood and bark and wood only in the total tree, total stem and the saw-log component of the stem. Ratio equations are also included for estimating saw-log stem weight or volume to any specified top diameter outside bark (d.o.b.). Wood and bark specific gravity, moisture content, bark content, and green weight per cubic foot are presented for the total tree and its components, by species and tree size classes.

Procedure

Field

Trees were selected from fully stocked, uneven-aged hardwood stands on the Chattahoochee National Forest in Georgia and the Pisgah and Nantahala National Forests in North Carolina. A stratified random sample of three to five trees per Z-inch d.b.h. class was selected at each sample location. Sample trees generally ranged from 5 to 20 or 22 inches d.b.h. Means and ranges in age and tree dimensions measured are shown in table 1 for each species and species group sampled. Stump height averaged 0.5 foot for trees 5.0 to 10.9 inches d.b.h. and 0.6 foot for trees > 11.0 inches d.b.h. Form class of the sawtimber-size trees (> 11.0 inches d.b.h.) ranged from 64 to 91 and averaged 80 for the soft hardwoods, and ranged from 61 to 90 and averaged 78 for the hard hardwoods.

Each tree was felled and measured for d.o.b. at 4-foot intervals up the stem Total height, and height to the saw-log top, 9-, 4-, and Z-inch d.o.b., and base of full live crown were also recorded. Cross-sectional disks of wood and bark were removed from the stem and branches of sample trees for laboratory determination of specific gravity, moisture content, bark percentage, energy value, and nutrient concentration. In all trees > 5.0 inches d.b.h. except sawtimber-quality trees (> 11.0 inches d.b.h. with a minimum of one 16-foot grade 3 log), disks were cut at the butt, d.b.h., and quarter-points to the 4-inch d.o.b. top and at the Z-inch top. In sawtimber trees, disks were removed at the butt, at each saw-log bucking point, and at the stem location where d.o.b. measured 9, 4, and 2 inches.

The branches of each tree were cut from the stem and weighed in four size categories: extra large (> 4.0 inches d.o.b.), large (2.0 to 3.9 inches d.o.b.), medium (0.6 to 1.9 inches d.o.b.), and small (< 0.5 inch d.o.b.). Three cross-sectional disks were cut from randomly selected branches in each size category for analysis in the laboratory.

The stem of each tree was weighed by components (saw logs, pulpwood, and topwood) and the branches of each tree were weighted by size category.

Laboratory

Specific gravity was computed on green volume and ovendry weight. Moisture content was computed on ovendry weight after samples were dried to a constant weight at 215 °F. Percentage of bark was determined from disks and based on the green weight of sample disks'. Moisture content, specific gravity, and percentage of bark in stem, branches, and total tree were calculated by weighting disk values in proportion to the volume of the component they represented. Weighted values for moisture content were used to convert component green weights to ovendry weight.

By using species diameter inside bark (d.i.b.) prediction equations, developed from d.o.b. and d.i.b. stem disk measurements, and the d.o.b. and height measurements taken at 4-foot intervals up the stem of each tree, the volume of wood in the stem to the saw log 9-inch, 4-inch, 2-inch, and tip were calculated by Smalian's formula. Green weight per cubic foot of stem bark and of branch wood and bark were calculated from weighted values for specific gravity and moisture content with the equation:

$$\text{Green weight per cubic foot} = \left[1 + \frac{MC}{100} \right] \cdot (\text{SG}) \cdot (\text{C}) \quad (1)$$

where: M = weighted moisture content in percent
 SG = weighted specific gravity
 C = 62.4 pounds (weight of water per cubic foot)

Cubic-foot volume of stem bark and branch wood and bark were computed by dividing green component weight by its green weight per cubic foot. Cubic-foot volume of stem wood and bark combined was computed by adding the volume of bark to the volume of wood.

Analysis

Regression equations were developed to predict green and dry weight and green volume of wood and bark in the total tree above stump, stem from butt to tip, and saw-log stem Independent variables were: diameter at height (D), total height (Th), saw-log merchantable height (Mh), and height to a 4-inch d.o.b. top (H4).

A logarithmic transformation (base 10) was used to obtain a relatively homogeneous variance, which is assumed in regression analysis. Two equations were developed for the d.b.h., d.b.h. and total height, and d.b.h. and height to 4-inch top--one for trees < 11.0 inches d.b.h. and one for trees \geq 11.0 inches d.b.h. The 11-inch point was not the optimum point to shift from one equation to the other for all species or tree components, -but it was the most desirable from a practical standpoint. Hardwood trees < 11 inches in diameter are classified as sapling or pole timber, and trees \geq 11 inches are classified as sawtimber. The procedure outlined in Draper and Smith (1981) for fitting two linear equations with a known point of intersection was used to develop the following equations:

$$\log Y_p = a + b \log X + E \quad (2)$$

$$\log Y_s = a + b \log (11^2 H) + c \log (D^2 / 11^2) + E \quad (3)$$

where: Y_p = predicted component weight or volume for trees
 < 11.0 inches d.b.h.

Y_s = predicted component weight or volume for trees
 ≥ 11.0 inches d.b.h.

$X = D^2, D^2 Th$ or $D^2 H4$

$H = Th$ or $H4$

$D = d. b. h.$

$E = experimental error$

$a, b, c = regression coefficients$

The following model was used for developing regression equations based on d.b.h. and saw-log merchantable height:

$$\log Y = a + b \log X_1 + c \log X_2 + E \quad (4)$$

where: Y = predicted component weight or volume

$$X_1 = D^2$$

$$X_2 = Mh$$

E = experimental error

a, b, c = regression coefficients

When logarithmic estimates are converted back to original units, they are biased downward because the antilogarithm of an estimated mean gives the geometric rather than the arithmetic mean (Cunia 1964). To adjust for this bias, a correction factor was computed and applied to each model by using Baskerville's (1972) procedure. The final equations, including correction factors, were:

$$Y = 10^{a + b \log(D^2) + c \log(Mh) + (S^2_{y,x} \log, 10)/2} \quad (5)$$

$$Y_p = 10^{a + b \log(D^2H) + (S^2_{y,x} \log, 10)/2} \quad (6)$$

$$Y_s = 10^{a + b \log(11^2H) + c \log(D^2/11^2) + (S^2_{y,x} \log, 10)/2} \quad (7)$$

Equations (5), (6), and (7) can be simplified to:

$$Y = a' (D^2)^b (Mh)^c \quad (8)$$

$$Y_p = a' (D^2H)^b \quad (9)$$

$$Y_s = a'' (D^2)^b (H)^c \quad (10)$$

where: $a' = 10^{a + (S^2_{y,x} \log_e 10)/2}$

$$a'' = a' (11^2)^b - c$$

$S^2_{y,x}$ = error mean square from regression analysis

Comparison of average deviations (actual minus predicted) by d.b.h. classes and the sums of the squared deviations for the single log-log equation and segmented log-log equation showed that segmented log-log equations (9) and (10) gave the best results for the d.b.h., d.b.h. and total height, and d.b.h. and height to 4-inch top independent variable combinations (Clark and others 1985). Equations (9) and (10) are more complex than a single equation, but the improved accuracy justified their use.

The following exponential ratio equation was used to estimate the proportion of predicted total-stem weight or volume to a specified top d.o.h.:

$$Y_R = e^a (d'' D^c) \quad (11)$$

where: Y_R = ratio of stem weight or volume to top d.o.h. to

predicted total stem

d = specified **stem top diameter in inches**

D = **tree diameter at breast height in inches**

a, b, c = regression **coefficients**

e = **base of natural log = 2.71828**

The exponential ratio model shown below was developed to estimate a ratio for expanding saw-log stem weight or volume to any d.o.b. top above the saw-log top.

$$Y_R = e^a \left[(Mh)^b ((1 - (\frac{d}{.78D})^2)^2)^c \right] \quad (12)$$

where: Y_R = **ratio of stem weight or volume to top d.o.b. to
saw-lot) stem**

Mh = **saw-log merchantable height in feet**

d = **specified top diameter in inches**

D = **tree diameter at breast height in inches**

.78 = **constant based on average form class**

a, b, c = **regression coefficients**

e = **base of natural log**

Results

Physical Properties of Sample Trees

The average specific gravity of wood and bark by tree component is shown in table 2 for individual species, soft hardwoods, hard hardwoods, and all trees combined. The average total-tree wood specific gravity of the soft hardwood species was 0.439 for poletimber (5.0 to 10.9 inches) and 0.440 for sawtimber (> 11.0 inches d.b.h.) compared with hard hardwood species, which averaged 0.598 for poletimber and 0.604 for sawtimber. Basswood had the lowest average total-tree wood specific gravity and blackgum the highest for the soft hardwoods group. In the hard hardwoods group, sweet birch had the lowest average total-tree wood specific gravity and hickory had the highest.

The average moisture content of wood and bark by tree component and sire class is shown in table 3 for the species and species groups sampled. Total-tree wood moisture content for the soft hardwoods averaged 105 percent for poletimber and 99 percent for sawtimber compared with hard hardwoods, which averaged 62 percent for poletimber and 67 percent for sawtimber. In the soft hardwoods group, basswood had the highest average total-tree moisture content compared with red maple, which had the lowest. In the hard hardwoods group, white oak had the lowest total-tree wood moisture content and northern redoak had the highest.

Table 4 shows the average proportion of bark in the tree, based on green weight of wood and bark, by tree component and size class for the species sampled.

Basswood had the highest bark percentage of the soft hardwoods and chestnut oak had the highest for the hard hardwoods. The percentage of stem weight in bark increased as stem d.o.b. decreased. Thus, poletimber trees generally had a higher proportion of the green weight in bark than did sawtimber trees, and branches had the highest proportion of green weight in bark.

The average green weight per cubic foot of wood, bark, and wood and bark combined, by tree component, for poletimber and sawtimber are shown in table 5. Because of the soft hardwood and hard hardwood species grouping, the average range of green weight for cubic foot of wood for the two groups is similar--49 to 67 pounds for the soft hardwoods and 52 to 67 pounds for the hard hardwoods. This is caused by the relatively high moisture content and specific gravity of blackgum in the soft hardwoods group and the low moisture content of white ash in the hard hardwoods group. The average green weight per cubic foot of wood for the soft hardwood species was 56 pounds for poletimber and 54 pounds for sawtimber compared with 62 pounds for pole and sawtimber hard hardwoods.

The average green weight of wood and bark per cubic foot of wood by tree component for poletimber and sawtimber-size trees is shown in table 6. The weight of wood and bark per cubic-foot volume of wood is a useful factor for estimating the volume of wood in a tree or its components when weight of wood and bark is known or for estimating green weight of wood and bark when volume of wood is known. The green weight of wood and bark per cubic foot of wood for the total tree averaged 68 pounds for poletimber and 65 pounds for sawtimber soft hardwoods compared with 75 pounds for poletimber and sawtimber hard hardwoods.

The average green weight of wood and bark per cubic foot of wood was highest for branches and decreased with increasing stem diameter (table 6).

Prediction Equations

A series of equations was developed to predict total-tree and tree component weight and volume for each species, the soft hardwood and hard hardwood groups, and all species combined. Equations were developed for predicting the green and dry weight of wood and bark combined and wood alone in the above-stump total tree. Stem equations were developed for estimating the green and dry weight of wood and bark combined, and wood alone for the total stem. Volume equations were also developed for wood and bark combined and wood alone in the above-stump total tree and total stem.

Since tree height is measured to different top limits by various organizations, equations were developed by using diameter (D) alone and in combination with total height (Th), height to 4-inch top (H_4), and merchantable height (Mh) as independent variables. Equation (9) was used to estimate the weight and volume of the total tree and stem for trees 5.0 to 10.9 inches d.b.h., and equation (10) was used for trees >11.0 inches d.b.h. when D alone, D and Th , or D and H_4 were the independent variables.

Equation (8) was used to estimate weight and volume of the total tree and saw-log merchantable stem for trees >11.0 inches d.b.h. when D and Mh were the independent variables. Equations based on D and Mh were developed only for species sampled sufficiently in the sawtimber diameter classes. Equations were developed for the soft hardwoods, hard hardwoods, and all species, and for yellow-poplar, white oak, hickory, black oak, chestnut oak, northern red oak, scarlet oak, and white oak.

Equation (11) was used to estimate the proportion of total-stem weight or volume in the stem to any d.o.b. top when stem weight or volume was estimated with D, D and Th, or D and H4 as the independent variables. Equation (12) was used to estimate a ratio for expanding estimated saw-log merchantable-stem weight or volume to any d.o.b. top above the saw-log top when D and Mh were the independent variables.

Equations that use D with Th or D with H4 fit the existing total-tree and total-stem weight and volume data well, based on the criteria of mean square error and absolute deviation of observed from predicted. Equations that use D and Mh fit existing saw-log merchantable-stem weight and volume data well. When average tree height and stem taper are similar to those of our sample trees, the equations with D alone will result in good estimates of the tree weight and volume. When average tree height by d.b.h. class are different from the sample trees, however, the equations that include a height variable should be applied directly or used to develop local weight-volume tables based on D alone.

Regression coefficients for estimating weight and volume are listed below, b.y independent variable and table number:

Independent variable	Weight	Volume
D alone	tables 7, 8	tables 9, 10
D and Th	tables 11, 12	tables 13, 14
D and H4	tables 15, 16	tables 17, 18
D and Mh	tables 19, 20	tables 21, 22

In addition to the regression coefficients, tables 7 through 2% contain the coefficients of determination and standard error (\log_{10}) for each equation.

Regression coefficients for estimating the proportion of the total-stem weight and volume in the stem to a specified d.o.b. top are given in tables 23 and 24. Table 23 contains coefficients for estimating ratios for stem green and dry weight of wood and bark combined and wood only, and table 24 contains the coefficients for stem volume of wood and bark combined and wood dL one. Equations for coefficients for expanding estimated saw-log merchantable-stem weight and volume are shown in tables 25 and 26, respectively.

How to Use Prediction Equations

The following examples illustrate how to use the equations in tables 7 through 26 to estimate the weight or volume of the total tree and its components.

This tabulation presents the tree data needed to estimate weight and volume when d.b.h. and Th are measured and equations (9) and (10) are used:

Example of trees < 11.0 inches d.b.h.

D = 10.0 inches

Th = 70 feet

Example **of trees \geq 11.0 inches**

$$D = 14.0 \text{ inches}$$

$$Th = 90 \text{ feet}$$

In estimate total-stem wood and bark green weight (Y_{STEMWB}) of a soft hardwood with these dimensions, the following equations would be selected from table 12 and solved as follows:

Trees < 11.0 inches d.b.h.--use equation (9)

$$\begin{aligned} Y_{STEMWB} &= a' (D^2 Th)^b \\ &= 0.19934 ((10^2)(70))^{0.94973} \\ &= 0.19934 (7000)^{0.94973} \\ &= 0.19934 (4,485.44) \end{aligned}$$

$$Y_{STEMWB} = 894 \text{ pounds}$$

Trees ≥ 11 inches d.b.h.--use equation (10)

$$\begin{aligned} Y_{STEMWB} &= a'' (D^2)^b (Th)^c \\ &= 0.16133 (14^2)^{0.99384} (90)^{0.94973} \\ &= 0.16133 (196) 3.99384 (90)^{0.94973} \\ &= 0.16133 (189.73) (71.78) \end{aligned}$$

$$Y_{STEMWB} = 7,197 \text{ pounds}$$

, The same mathematical procedure shown above would be used to solve equations (9) or (10) for any of the tree component equations in tables 7 through 22.

To estimate the proportion of total-stem green weight of wood and bark in the stem of a 1-inch d.b.h. tree to a 4-inch d.o.b. top (Y_R), the following soft hardwood ratio regression coefficients would be selected from table 23 and solved by using equation (11) as shown below. The same equation is used for all size trees.

$$\begin{aligned} Y_R &= e^a (d)^b (D)^c \\ &= 2.71828 \left[-2.21340 (4)^{3.69663} (10) - 4.00734 \right] \\ &= 2.71828 \left[-2.21340 (168.11) (0.000098) \right] \\ &= 2.71828^{-0.03647} \\ Y_R &= 0.964 \end{aligned}$$

$$\begin{aligned}\text{Stem weight to 4-inch top} &= (\gamma_{\text{STEMWB}}) (\gamma_R) \\ &= 894 (0.964)\end{aligned}$$

Stem weight to 4-inch top = 862 pounds

The procedure shown above can be used to estimate the proportion of total stem in the stem to any d.o.b. top by substituting for d in equation (11).

The following tabulation shows the tree data needed to estimate weights and volumes when d.b.h. and M_h are measured and equation (8) is used.

$$D = 14.0 \text{ inches d.b.h.}$$

$$M_h = 2.0 \text{ logs}$$

To use equation (8), M_h must be in feet, thus:

$$M_h = 33.1 \text{ feet} = (2.0 \text{ logs}) (16.3 \text{ ft./log}) + (0.5 \text{ ft for stump})$$

To estimate the green weight of wood and bark in the saw-log merchantable stem (γ_{SAWWB}) of a soft hardwood tree, by using equation (8) the following coefficients would be selected from table 20 and solved as follows:

$$\begin{aligned}-\gamma_{\text{SAWWB}} &= a' (D^2)b (M_h)c \\ &= 0.55968 (14^2)^{0.97608} (33.1)^{0.76439} \\ &= 0.55968 (1.73.75) (14.51)\end{aligned}$$

$$\gamma_{\text{SAWWB}} = 1,403 \text{ pounds}$$

The same mathematical procedure shown above would be used to solve equation (8) for any sawtimber tree component equation in tables 13 through 22.

To estimate a ratio (γ_R) for expanding estimated saw-log merchantable-stem green weight of wood and bark of the previous tree to weight to a 4-inch d.o.b. top, the following soft hardwood ratio equation would be selected from table 25 and solved by using equation (12) as shown below.

$$\begin{aligned}\gamma_R &= e^a \left[(M_h)^b ((1 - (\frac{d}{780})^2)^2)^c \right] \\ &= 2.7182820.03667 \left[(33.1)^{-1.15011} ((1 - (\frac{4}{78(14)})^2)^2)^{0.30738} \right] \\ &= 2.7182820.03667 (0.01787) (0.91524) \\ &= 2.718280.32764\end{aligned}$$

$$\gamma_R = 1.388$$

$$\text{Stem weight to 4-inch top} = (Y_{SAWWB}) (Y_R)$$

$$= 1,403 \text{ (1.388)}$$

$$\text{Stem weight to 4-inch top} = 1,947 \text{ pounds}$$

The tree components predicted by using the equations provided can be used to calculate additional tree components. For example, to estimate the weight or volume of the crown (branches and topwood) subtract estimated weight of the stem to a specified d.o.b. top from total-tree weight of wood and bark. The weight or volume of bark alone can also be estimated by subtracting component weight or volume of wood from wood and bark.

Similar-size trees may vary in weight and volume because of differences in crown size, stem taper, and weight per cubic foot. Therefore, these equations should be applied only to trees growing in natural, fully stocked stands with tree dimensions and weight per cubic foot similar to the tree sampled.

Literature Cited

Baskerville, G.L. Use of logarithmic regression in the estimation of plant biomass. *Canadian Journal of Forest Research* 2:49-53; 1972.

Clark, Alexander, III; Mise, H. David; Phillips, Douglas R.; Frederick, Douglas J. Use of segmented log-log equations to estimate tree biomass. In: Saucier, Joseph R., ed. *Proceedings of the 1984 southern forest biomass workshop. Sixth annual meeting of the Southern Forest Biomass Working Group*; 1984 June 5-7; Athens, GA. Asheville, NC: U.S. Department of Agriculture, Forest Service, Southeastern Forest Experiment Station; 1985:51-57.

Cunia, T. Weighted least squares method and construction of volume tables. *Forest, Science* 10: 180-191; 1964.

Draper, N.R.; Smith, H. *Applied regression analyses*. 2d ed. New York: John Wiley & Sons; 1981. 709 pp.



TABLES



Table 1 -- Mean and range of tree age and measurements, by species and tree size class

Tree size class (inches)	Sample trees	Age		D.b.h.		Total height		Height to 4- inch d.o.b. top		Height to saw- log merchantable top		D.o.b. at saw- log merchantable top		
		Average	Range	Average	Range	Average	Range	Average	Range	Average	Range	Average	Range	
Number												Inches		
Feet												Inches		
SOFT HARDWOODS														
5.0-10.9	60	55	16-146	8.1	5.1-10.7	67	34-102	38	12-73	--	--	--	--	
>11.0	68	77	50-198	15.8	11.0-25.6	98	58-147	77	39-129	50	16-99	10.5	7.8-18.0	
All trees	128	67	16-198	12.2	5.1-25.6	84	34-147	58	12-129	50	16-99	10.5	7.8-18.0	
BASSWOOD														
5.0-10.9	9	60	46-75	8.0	5.6-10.5	72	63-82	41	23-59	--	--	--	--	
>11.0	9	76	52-100	14.1	11.8-16.5	91	80-106	69	57-82	27	16-37	12.0	9.4-15.4	
All trees	18	68	46-100	11.1	5.6-16.5	82	63-106	55	23-32	27	16-37	12.0	9.4-i5.4	
BLACKGUM														
5.0-10.9	9	97	80-146	8.0	5.7-10.0	49	34-58	27	14-41	--	--	--	--	
>11.0	9	140	72-198	14.6	12.0-17.8	73	58-100	54	39-78	42	30-67	9.3	9.0-10.9	
All trees	18	119	72-198	11.3	5.7-17.8	61	34-100	40	14-78	42	30-67	9.3	9.0-10.9	
RED MAPLE														
5.0-10.9	18	59	42-73	8.0	5.1-10.7	65	47-86	36	12-60	--	--	--	--	
>11.0	12	65	50-89	14.2	12.0-16.8	83	63-104	58	43-80	28	9-50	11.0	8.0-14.9	
All trees	30	61	42-89	10.5	5.1-16.8	72	47-104	45	12-80	28	9-50	11.0	8.0-14.9	
YELLOW POPLAR														
5.0-10.9	24	36	16-75	8.1	5.6-10.7	73	51-102	42	17-73	--	--	--	--	
>11.0	38	66	50-76	17.0	11.0-25.6	111	84-147	90	59-129	64	28-99	10.2	7.8-18.2	
All trees	62	54	16-76	13.6	5.6-25.6	97	51-147	71	17-129	64	28-99	10.2	7.8-18.2	
HARD HARDWOODS														
5.0-10.9	143	60	19-114	8.1	5.0-10.9	65	36-92	39	9-67	--	--	--	--	
>11.0	204	91	45-175	16.3	11.0-24.7	90	61-120	70	40-104	42	16-78	11.6	8.1-19.0	
All trees	347	78	19-175	12.9	5.0-24.7	80	36-120	57	9-104	42	16-78	11.6	8.1-19.0	
WHITE ASH														
5.0-10.9	27	57	25-85	8.0	5.0-10.3	67	44-84	42	15-67	--	--	--	--	
>11.0	25	87	54-147	15.1	11.0-21.8	91	73-119	71	52-103	35	16-73	12.4	9.0-19.0	
All trees	52	72	25-147	11.4	5.0-21.8	79	44-119	56	15-103	35	16-73	12.2	9.0-19.0	

Continued

Table 1.--Mean and range of tree age and measurements, by species and tree size class--Continued

Tree size class (inches)	Sample trees	Age		D. b. h.		Total height		Height to 4- inch d. o. b. top		Height to saw- log merchantable top		
		Average	Range	Average	Range	Average	Range	Average	Range	Average	Range	
Number												
Inches												
Feet												
SWEET BIRCH												
5.0-10.9	9	47	32-73	8.1	5.8-10.5	62	53-74	33	20-46	--	--	
>11.0	12	74	51-105	15.0	11.9-18.5	79	67-98	56	46-73	23	16-39	
All trees	21	62	32-105	12.1	5.8-18.5	72	53-98	46	20-73	23	16-39	
BLACK LOCUST												
5.0-10.9	9	24	19-39	8.1	5.6-10.2	57	36-68	34	22-48	--	--	
>11.0	9	50	45-79	13.8	11.6-16.4	81	65-99	61	45-86	35	25-45	
All trees	18	37	19-79	11.0	5.6-16.4	69	36-99	48	22-86	35	25-45	
HICKORY												
5.0-10.9	20	75	26-114	8.1	5.1-10.9	67	42-92	40	12-65	--	--	
>11.0	34	115	74-175	16.3	11.6-23.1	93	72-120	74	53-104	44	17-74	
All trees	54	99	26-175	13.3	5.1-23.1	84	42-120	62	12-104	44	17-74	
BLACK OAK												
5.0-10.9	9	72	41-109	8.3	6.2-10.5	63	44-80	37	16-55	--	--	
>11.0	18	106	68-170	17.0	11.8-21.8	84	74-97	64	48-77	38	26-57	
All trees	26	94	41-170	13.8	6.2-21.8	77	44-97	55	16-77	38	26-57	
CHESTNUT OAK												
5.0-10.9	18	80	46-107	8.2	5.6-10.9	62	47-85	38	18-57	--	--	
>11.0	32	104	68-151	16.4	11.5-22.3	87	61-115	70	46-94	45	28-66	
All trees	50	95	46-151	13.4	5.6-22.3	78	47-115	58	18-94	45	28-66	
NORTHERN RED OAK												
5.0-10.9	33	48	35-55	8.3	5.9-10.9	70	53-86	43	18-65	--	--	
>11.0	38	74	50-114	17.1	11.1-24.7	96	67-118	74	50-98	50	25-78	
All trees	71	62	35-114	13.0	5.9-24.7	84	53-118	60	18-98	50	25-78	
SCARLET OAK												
5.0-10.9	9	65	47-81	8.0	5.7-10.2	56	44-72	32	13-53	--	--	
>11.0	18	87	52-124	17.0	11.7-22.2	87	63-105	66	40-87	44	24-54	
All trees	27	no	47-124	14.0	5.7-22.2	76	44-105	55	13-87	44	24-54	

Table 1.--Mean and range of tree age and measurements, by species and tree size class--Continued

Tree size class (inches)	Sample trees	Age		D.b.h.		Total height		Height to 4- inch d.o.b. top		Height to saw- log merchantable top		D.o.b. at saw- log merchantable top				
		Average	Range	Average	Range	Average	Range	Average	Range	Average	Range	Average	Range			
Number												Feet				
 Inches 																
WHITE OAK																
5.0-10.9	9	70	54-86	16.7	5.1-10.3	61	38-84	36	9-60	--	--	11.9	--			
>11.0	19	91	62-130		11.6-21.7	94	72-110	72	53-85	46	34-64	11.9	8.4-18.0			
All trees	28	84	54-130	13.9	5.1-21.7	84	38-110	60	9-85	46	34-64	11.9	8.4-18.0			
ALL SPECIES																
>11.00.9	203	89	28-146	16.2	15.0-20.0	92	38-102	39	39-129	44	16-99	11.3	7.8-19.0			
All trees	475	75	16-198	12.7	5.0-25.6	81	34-147	57	9-129	44	16-99	11.3	7.8-19.0			

Table 2.--Average specific gravity of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains

Tree size class (inches)	Average and standard deviation							
	'Total tree	Stem						
		Butt to 9-inch top	9-inch to d-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip	Branches	
SOFT HARDWOODS								
Wbod								
5.0-10.9 ≥11.0	0.439 ± 0.073 0.440 ± 0.062	0.440 -- 0.440 ± 0.064	0.451 ± 0.061 --	0.442 ± 0.075 0.440 ± 0.063	0.436 ± 0.070 0.456 ± 0.063	0.440 ± 0.074 0.440 ± 0.063	0.440 ± 0.070 0.441 ± 0.063	
Bark								
5.0-10.9 ≥11.0	0.441 ± 0.094 0.400 ± 0.088	0.404 -- 0.404 ± 0.099	0.425 ± 0.086 --	0.457 ± 0.101 0.407 ± 0.097	0.437 ± 0.104 0.413 ± 0.087	0.462 ± 0.094 0.408 ± 0.035	n. 379 ± 0.121 0.371 ± 0.092	
Wbod and Bark								
5.0-10.9 ≥11.0	0.440 ± 0.072 0.434 ± 0.061	0.434 -- 0.434 ± 0.063	0.446 ± 0.058 --	0.443 ± 0.073 0.434 ± 0.062	0.436 ± 0.068 0.448 ± 0.059	0.444 ± 0.073 0.435 ± 0.063	0.421 ± 0.073 0.426 ± 0.062	
BASSWOOD								
Wbod								
5.0-10.9 ≥11.0	0.353 ± 0.022 n.364 ± 0.033	0.371 -- 0.371 ± 0.040	0.362 ± 0.022 --	0.359 ± 0.024 0.368 ± 0.035	0.345 ± 0.017 1.354 ± 0.030	0.357 ± 0.024 0.368 ± 0.034	0.324 ± 0.008 0.339 ± 0.031	
Bark								
5.0-10.9 ≥11.0	0.418 ± 0.023 0.411 ± 0.015	0.422 ± 0.018 --	0.413 -- 0.413 ± 0.017	n. 471 ± 0.023 0.419 ± 0.017	0.421 ± 0.026 0.407 ± 0.025	0.423 ± 0.023 0.418 ± 0.017	0.406 ± 0.022 0.396 ± 0.018	
Wbod and Bark								
5.0-10.9 ≥11.0	n. 369 ± 0.017 0.374 ± 0.027	0.378 ± 0.034 --	0.372 ± 0.019 --	0.370 ± 0.021 0.376 ± 0.029	0.366 ± 0.013 n. 369 ± 0.026	0.370 ± 0.020 0.376 ± 0.029	0.354 ± 0.010 0.359 ± 0.024	
BLACKGUM								
Wbod								
5.0-10.9 ≥11.0	0.524 ± 0.027 0.509 ± 0.054	0.514 ± 0.056 --	0.497 ± 0.054	0.528 ± 0.034 0.511 ± 0.056	0.518 ± 0.028 0.523 ± 0.057	0.526 ± 0.032 0.511 ± 0.056	0.521 ± 0.015 I. 500 ± 0.049	
Bark								
5.0-10.9 ≥11.0	0.471 ± 0.029 0.448 ± 0.048	0.437 ± 0.074 --	0.435 ± 0.083 --	0.455 ± 0.039 0.435 ± 0.076	0.465 ± 0.038 0.464 ± 0.054	0.457 ± 0.037 0.436 ± 0.074	3.494 ± 0.031 0.460 ± 0.024	

Continued

Table 2...Average specific gravity of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation ¹ Stem						Branches
		Butt to 9-inch top	-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip		
Wood and Bark								
5.0-10.9	0.513 ± 0.023	--	--	0.512 ± 0.026	0.503 ± 0.024	0.516 ± 0.027	0.511 ± 0.015	
>11.0	0.502 ± 0.041	0.504 ± 0.041	0.486 ± 0.038	0.500 ± 0.041	0.508 ± 0.035	0.505 ± 0.046	0.488 ± 0.036	
RED MAPLE								
Wood								
5.0-10.9	0.507 ± 0.022	--	--	0.512 ± 0.025	0.496 ± 0.024	0.509 ± 0.024	0.497 ± 0.026	
>11.0	0.515 ± 0.032	0.516 i-0.036	0.518 ± 0.032	0.516 ± 0.034	0.517 ± 0.031	0.516 ± 0.034	0.515 ± 0.031	
Bark								
5.0-10.9	0.559 ± 0.038	--	--	0.594 ± 0.036	0.566 ± 0.045	0.590 ± 0.035	0.482 ± 0.051	
>11.0	0.544 ± 0.033	0.572 i-0.039	0.573 i-0.043	0.572 ± 0.039	0.555 ± 0.026	0.571 ± 0.038	0.504 ± 0.039	
Wood and Bark								
5.0-10.9	0.516 ± 0.020	--	--	0.523 ± 0.023	0.508 ± 0.020	0.520 ± 0.022	0.491 ± 0.024	
>11.0	0.520 ± 0.026	0.522 ± 0.032	0.526 ± 0.025	n. 522 ± 0.031	n. 524 ± 0.024	0.523 ± 0.030	0.511 ± 0.027	
YELLOW POPLAR								
Wood								
5.0-10.9	0.389 ± 0.028	--	--	0.388 ± 0.028	0.393 ± 0.034	0.387 ± 0.028	0.410 ± 0.024	
>11.0	0.418 ± 0.030	0.414 ± 0.030	0.440 i-0.042	0.415 ± 0.030	0.445 ± 0.034	0.416 ± 0.030	0.438 ± 0.033	
Bark								
5.0-10.9	0.350 ± 0.029	--	--	0.367 ± 0.029	0.336 ± 0.037	0.382 ± 0.032	0.248 ± 0.057	
>11.0	0.341 ± 0.047	0.340 ± 0.047	0.379 ± 0.046	0.344 ± 0.047	0.358 ± 0.050	0.346 ± 0.045	0.312 ± 0.059	
Wood and Bark								
5.0-10.9	0.383 ± 0.025	--	--	0.385 ± 0.026	0.385 ± 0.029	0.387 ± 0.026	0.360 ± 0.024	
>11.0	0.406 ± 0.028	0.403 ± 0.028	0.429 i-0.038	0.405 ± 0.028	0.428 ± 0.032	0.405 ± 0.028	0.400 ± 0.036	
HARD HARDWOODS								
Wood								
5.0-10.9	0.598 ± 0.048	--	--	0.596 ± 0.053	0.619 ± 0.037	0.598 ± 0.047	0.606 ± 0.039	
>11.0	0.604 ± 0.041	0.596 i-0.046	0.616 ± 0.044	0.598 ± 0.045	0.630 ± 0.037	0.598 ± 0.045	0.622 ± 0.040	

Continued

Table 2.--Average specific gravity of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation						Branches
		Butt to 0-inch top	9-inch to d-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip		
stem								
5.0-10.9	0.502 ± 0.096	--	--	0.510 ± 0.119	0.514 ± 0.087	0.510 ± 0.113	0.476 ± 0.070	
>11.0	0.536 ± 0.093	0.545 ± 0.109	0.558 ± 0.107	0.548 ± 0.108	0.532 ± 0.077	0.548 ± 0.107	0.516 ± 0.079	
Rark								
5.0-10.9	0.582 ± 0.043	--	--	0.578 ± 0.053	0.592 ± 0.034	0.584 ± 0.044	0.563 ± 0.036	
>11.0	0.594 ± 0.033	0.586 ± 0.039	0.601 ± 0.040	0.587 ± 0.038	0.600 ± 0.034	0.591 ± 0.038	0.588 ± 0.038	
Wood and Bark								
5.0-10.9	0.589 ± 0.031	--	--	0.589 ± 0.035	0.613 ± 0.035	0.590 ± 0.034	0.590 ± 0.028	
>11.0	0.579 ± 0.040	0.572 ± 0.043	0.603 ± 0.043	0.576 ± 0.042	0.622 ± 0.044	0.576 ± 0.042	0.598 ± 0.044	
WHITE ASH								
Wood								
5.0-10.9	0.407 ± 0.041	--	--	0.375 ± 0.056	0.441 ± 0.039	0.383 ± 0.053	0.461 ± 0.032	
>11.0	0.407 ± 0.044	0.344 ± 0.043	0.405 ± 0.055	n. 387 ± 0.044	0.446 ± 0.047	0.388 ± 0.044	0.440 ± 0.046	
Bark								
5.0-10.9	n. 562 ± 0.031	--	--	0.551 ± 0.036	n. 569 ± 0.033	0.558 ± 0.034	0.549 ± 0.027	
>11.0	0.556 ± 0.037	0.544 ± 0.038	n. 562 ± 0.045	n. 546 ± 0.037	0.567 ± 0.046	0.552 ± 0.039	0.549 ± 0.044	
Wood and Rat-k								
SWEET BIRCH								
Wood								
5.0-10.9	0.531 ± 0.095	--	--	0.541 ± 0.107	0.608 ± 0.023	0.555 ± 0.080	0.571 ± 0.021	
>11.0	0.602 ± 0.025	0.601 ± 0.027	0.611 ± 0.027	0.602 ± 0.025	0.618 ± 0.029	0.602 ± 0.026	0.601 ± 0.026	
Rark								
5.0-10.9	0.556 ± 0.084	--	--	0.619 ± n. 144	0.633 ± 0.030	0.624 ± 0.105	0.511 ± 0.026	
>11.0	0.663 ± 0.027	0.716 ± 0.025	0.719 -- 0.030	0.717 ± 0.025	0.679 ± 0.026	0.716 ± 0.025	0.594 ± 0.039	
Wood and Bark								
5.0-10.9	0.536 ± 0.092	--	--	0.550 ± 0.112	0.612 ± 0.020	0.564 ± 0.082	0.551 ± 0.019	
>11.0	0.614 ± 0.020	0.616 ± 0.023	n. 628 ± 0.022	0.617 ± 0.022	0.630 ± 0.022	0.618 ± 0.021	0.598 ± 0.025	

Continued

Table 2.--Average specific gravity of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class <u>(inches)</u>	Total tree	Average and standard deviation						Branches		
		Stem								
		Butt to 9-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip				
BLACK LOCUST										
Wbod										
5.0-10.9	0.600 ± 0.059	--			0.583 ± 0.087	0.648 ± 0.016	0.596 ± 0.070	0.621 ± 0.046		
≥11.0	0.655 ± 0.032	0.648 ± 0.037	0.664 ± 0.033		0.652 ± 0.035	0.676 ± 0.033	0.652 ± 0.035	0.666 ± 0.026		
Bark										
5.0-10.9	0.289 ± 0.026	--			0.266 ± 0.040	0.328 ± 0.018	0.277 ± 0.032	0.329 ± 0.021		
≥11.0	0.305 ± 0.027	0.282 ± 0.024	0.317 ± 0.030		0.293 ± 0.025	0.346 ± 0.030	0.295 ± 0.025	0.335 ± 0.031		
Wbod and Bark										
5.0-10.9	0.554 ± 0.055	--			0.508 ± 0.079	0.564 ± 0.029	0.551 ± 0.068	0.514 ± 0.037		
≥11.0	0.605 ± 0.025	0.561 ± 0.020	0.568 ± 0.021		0.565 ± 0.017	0.570 ± 0.026	0.606 ± 0.027	0.542 ± 0.024		
HICKORY										
Wbod										
5.0-10.9	0.657 ± 0.033	--			0.660 ± 0.031	0.666 ± 0.044	0.659 ± 0.033	0.640 ± 0.051		
≥11.0	0.648 ± 0.033	0.646 ± 0.039	0.661 ± 0.038		0.649 ± 0.037	0.657 ± 0.047	0.649 ± 0.036	0.647 ± 0.037		
Bark										
5.0-10.9	0.503 ± 0.027	--			0.523 ± 0.028	0.493 ± 0.031	0.519 ± 0.027	0.445 ± 0.040		
≥11.0	0.531 ± 0.036	0.550 ± 0.039	0.561 ± 0.037		0.552 ± 0.036	0.520 ± 0.032	0.552 ± 0.036	0.497 ± 0.044		
Wbod and Bark										
5.0-10.9	0.632 ± 0.030	--			0.636 ± 0.030	0.625 ± 0.036	0.636 ± 0.032	0.574 ± 0.040		
≥11.0	0.629 ± 0.029	0.631 ± 0.034	0.642 ± 0.031		0.634 ± 0.031	0.615 ± 0.037	0.635 ± 0.031	0.599 ± 0.033		
BLACK OAK										
Wbod										
5.0-10.9	0.579 ± 0.025	--			0.570 ± 0.026	0.606 ± 0.024	0.572 ± 0.025	0.623 ± 0.034		
≥11.0	0.573 ± 0.038	0.556 ± 0.044	0.579 ± 0.039		0.560 ± 0.044	0.623 ± 0.029	0.560 ± 0.044	0.613 ± 0.033		
Bark										
5.0-10.9	0.533 ± 0.035	--			0.552 ± 0.038	0.538 ± 0.042	0.550 ± 0.038	0.433 ± 0.048		
≥11.0	0.573 ± 0.032	0.584 ± 0.032	0.601 ± 0.035		0.587 ± 0.030	0.565 ± 0.037	0.586 ± 0.030	0.542 ± 0.052		

Continued

Table 2...Average specific gravity of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation						Branches	
		S t e m			Butt to J-inch toe	4-inch to J-inch toe	4-inch to tio		
		Butt to 9-inch toe	9-inch to 4-inch toe	4-inch toe					
Wood and Bark									
5.0-10.9	0.570 ± 0.022				0.566 ± 0.022	0.591 ± 0.023	0.569 ± 0.021	0.557 ± 0.036	
≥11.0	0.574 ± 0.030	0.561 ± 0.036	0.583 ± 0.025		0.564 ± 0.035	0.608 ± 0.021	0.564 ± 0.035	0.591 ± 0.020	
CHESTNUT OAK									
Wood									
5.0-10.9	0.608 ± 0.022				0.612 ± 0.022	0.603 ± 0.026	0.610 ± 0.022	0.592 ± 0.033	
≥11.0	0.620 ± 0.023	0.620 ± 0.023	0.622 ± 0.031		0.620 ± 0.023	0.620 ± 0.033	0.620 ± 0.023	0.620 ± 0.052	
Bark									
5.0-10.9	0.500 ± 0.039				0.508 ± 0.045	0.488 ± 0.041	0.505 ± 0.044	0.474 ± 3.033	
≥11.0	0.506 ± 3.035	0.515 ± 0.042	0.507 ± 0.042		0.513 ± 0.042	0.497 ± 0.037	0.513 ± 0.041	0.488 ± 0.031	
Wood and Bark									
5.0-10.9	0.585 ± 0.025				0.586 ± 0.028	0.567 ± 0.026	0.589 ± 0.026	0.549 ± 0.029	
≥11.0	0.598 ± 0.021	0.599 ± 0.021	U.589 ± 0.028		0.598 ± 0.022	0.576 ± 0.025	0.602 ± 0.021	0.572 ± 0.040	
NORTHERN RED OAK									
Wood									
5.0-10.9	0.581 ± 0.020				0.577 ± 0.020	0.606 ± 0.025	0.578 ± 0.019	0.600 ± 0.031	
≥11.0	0.580 ± 0.021	0.568 ± 0.022	0.608 ± 0.026		0.571 ± 0.022	0.609 ± 0.009	0.571 ± 0.022	0.610 ± 0.022	
Bark									
5.0-10.9	0.610 ± 0.022				0.624 ± 0.025	0.607 ± 0.026	0.623 ± 0.024	0.561 ± 0.037	
≥11.0	0.623 ± 0.032	0.634 ± 0.038	0.658 ± 0.038		0.636 ± 0.036	0.590 ± 0.006	0.635 ± 0.036	0.596 ± 0.056	
Wood and Bark									
5.0-10.9	0.586 ± 0.018				0.583 ± 0.018	0.606 ± 0.021	0.585 ± 0.017	0.590 ± 6.229	
≥11.0	0.587 ± 0.019	0.576 ± 0.021	0.616 ± 0.025		0.579 ± 0.022	0.608 ± 0.307	0.579 ± 0.022	0.607 ± 0.024	
SCARLET OAK									
Wood									
5.0-10.9	0.576 ± 0.029				0.563 ± 0.035	3.594 ± 0.026	0.565 ± 0.035	0.619 ± 0.011	
≥11.0	0.578 ± 0.024	0.558 ± 0.025	0.564 ± 0.027		0.559 ± 0.025	0.635 ± 0.025	0.560 ± 0.025	0.629 ± 0.027	

Continued

Table Z--Average specific gravity of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation						Branches	
		Stem							
		Butt to 9-inch top	9-inch to 4-inch top	Butt to 4-inch top	d-inch to tip	Butt to tip			
Bark									
5.0-10.9	0.555 ± 0.045	--		0.595 ± 0.028	0.555 ± 0.043	0.590 ± 0.030	0.476 ± 0.067		
<u>>11.0</u>	0.613 ± 0.037	0.635 ± 0.035	0.639 ± 0.037	0.636 ± 0.034	0.591 ± 3.037	0.635 ± 0.034	0.575 ± 0.044		
Wood and Bark									
5.0-10.9	0.572 ± 0.021	--		0.568 ± 0.029	0.587 ± 0.024	0.569 ± 0.028	0.572 ± 0.027		
<u>>11.0</u>	0.584 ± 0.019	0.568 ± 0.021	0.575 ± 0.022	0.569 ± 0.021	0.623 ± 0.021	0.570 ± 0.021	0.614 ± 0.022		
WHITE OAK									
Wood									
5.0-10.9	0.629 ± 0.026	--		0.630 ± 0.028	0.633 ± 0.021	0.630 ± 0.026	0.623 ± 0.039		
<u>>11.0</u>	0.608 ± 0.026	0.595 ± 0.028	0.623 ± 0.034	0.596 ± 0.028	0.637 ± 0.031	0.596 ± 0.028	0.637 ± 0.033		
Bark									
5.0-10.9	0.477 ± 0.038	--		0.492 ± 0.043	0.490 ± 0.045	0.490 ± 0.044	0.443 ± 0.036		
<u>>11.0</u>	0.518 ± 0.033	0.533 ± 0.045	0.555 ± 0.040	0.536 ± 0.040	0.531 ± 0.029	0.536 ± 0.040	0.494 ± 0.036		
Wood and Bark									
5.0-10.9	0.607 ± 0.025	--		0.610 ± 0.027	0.598 ± 0.022	0.612 ± 0.025	0.562 ± 0.034		
<u>>11.0</u>	0.594 ± 0.022	0.587 ± 0.023	0.609 ± 0.029	0.588 ± 0.023	0.605 ± 0.024	0.589 ± 0.024	0.594 ± 0.029		
ALL SPECIES									
Wood									
5.0-10.9	0.550 ± 0.092	--		0.550 ± 0.093	0.565 ± 0.097	0.551 ± 0.092	0.557 ± 0.091		
<u>>11.0</u>	0.563 ± 0.085	0.557 ± 0.085	0.574 ± 0.087	0.558 ± 0.085	0.586 ± 0.088	0.551 ± 0.091	0.579 ± 0.089		
Bark									
5.0-10.9	0.484 ± 0.099	--		0.494 ± 0.116	0.491 ± 0.099	0.496 ± 0.110	0.447 ± 0.098		
<u>>11.0</u>	0.502 ± 0.109	0.510 ± 0.123	0.524 ± 0.118	0.513 ± 0.122	0.502 ± 0.095	0.513 ± 0.120	0.481 ± 0.102		
Wood and Bark									
5.0-10.9	0.540 ± 0.054	--		0.538 ± 3.086	0.546 ± 0.085	0.542 ± 0.084	0.521 ± 0.082		
<u>>11.0</u>	0.554 ± 0.081	0.547 ± 0.081	0.562 ± 0.081	0.549 ± 0.080	0.562 ± 0.078	0.552 ± 0.081	0.547 ± 0.084		

Table 3...Average moisture content of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains

Tree size class (inches)	Total tree	Average and standard deviation					
		Stem					
		Butt to 9-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip	Branches
Percent							
SOFT HARDWOODS							
Wbod							
5.0-10.9 ≥11.0	105 ± 19.1 99 ± 15.8	98 -- 98 ± 15.8	95 -- 95 ± 16.6	105 ± 19.9 98 ± 15.6	103 ± 19.0 104 ± 18.3	105 ± 19.1 98 ± 15.6	107 ± 22.0 107 ± 21.2
Bark							
5.0-10.9 ≥11.0	109 ± 48.7 96 ± 27.7	87 -- 87 ± 26.6	84 i-22.6	96 ± 43.6 86 ± 25.7	125 ± 66.5 125 ± 48.1	106 ± 55.4 88 ± 26.7	164 ± 99.4 145 ± 61.6
Wbod and Bark							
5.0-10.9 ≥11.0	104 ± 20.5 98 ± 14.9	96 -- 96 ± 15.0	93 -- 93 ± 14.8	103 ± 20.7 95 ± 14.6	105 ± 21.3 106 ± 20.1	105 ± 21.6 96 ± 14.7	124 ± 37.7 119 ± 27.8
BASSWOOD							
Wbod							
5.0-10.9 ≥11.0	126 ± 16.2 119 ± 11.7	120 -- 120 ± 12.9	111 -- 111 ± 13.5	125 ± 17.9 118 ± 12.1	123 ± 12.7 115 ± 13.2	125 ± 17.2 118 ± 12.0	136 ± 13.6 129 ± 14.8
Bark							
5.0-10.9 ≥11.0	97 ± 6.6 96 ± 6.8	85 -- 85 ± 9.9	86 ± 10.3	90 ± 4.8 85 ± 9.7	101 ± 9.8 104 ± 11.8	91 ± 4.3 85 ± 9.6	113 ± 9.9 119 ± 11.6
Wbod and Bark							
5.0-10.9 ≥11.0	118 ± 12.0 114 ± 9.9	115 -- 115 ± 11.6	106 i-11.2	118 ± 15.1 113 ± 10.6	117 ± 8.2 112 ± 11.9	118 ± 14.1 113 ± 10.6	127 ± 8.0 126 ± 12.9
BLACKGUM							
Wbod							
5.0-10.9 ≥11.0	107 ± 7.8 98 ± 14.2	94 -- 94 ± 12.2	98 -- 98 ± 18.0	106 ± 9.1 95 ± 13.9	110 ± 7.5 101 ± 16.4	106 ± 8.8 95 ± 14.0	112 ± 6.3 109 ± 16.5
Bark							
5.0-10.9 ≥11.0	54 ± 7.6 52 ± 9.1	49 -- 49 ± 13.5	50 ± 13.0	49 ± 8.3 49 ± 13.2	56 ± 6.4 61 ± 9.7	49 ± 8.2 49 ± 12.9	63 ± 6.0 59 ± 7.7
Wbod and Bark							
5.0-10.9 ≥11.0	95 ± 6.2 a7 ± 7.4	85 -- 85 ± 6.2	87 -- 87 ± 11.6	93 ± 6.3 86 ± 7.5	94 ± 5.5 88 ± 7.8	97 ± 7.1 88 ± 9.1	96 ± 7.2 93 ± 11.2
RED MAPLE							
Wbod							
5.0-10.9 ≥11.0	a3 ± 5.3 76 ± 7.3	77 -- 77 ± 7.2	73 -- 73 ± 7.6	83 ± 6.5 76 ± 7.1	83 ± 6.9 76 ± 8.8	83 ± 6.2 76 ± 7.1	a2 ± 11.9 77 ± 10.4

Continued

Table 3...Average moisture content of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Average and standard deviation									
	Total tree	Butt to Y-inch top		9-inch to 4-inch top		Butt to 4-inch top		Butt to tip	Butt to tip	Branches
		Percent	Percent	Percent	Percent	Percent	Percent			
Bark										
5.0-10.9	74 ± 9.4	--	--	64 ± 7.0	77 ± 11.9	66 ± 6.9	95 ± 14.4			
>11.0	72 ± 7.3	61 ± 7.6	64 ± 9.3	62 ± 7.2	78 ± 8.4	62 ± 7.1	85 ± 11.5			
Wood and Bark										
5.0-10.9	81 ± 4.8	--	--	81 ± 5.2	82 ± 6.2	81 ± 5.1	85 ± 12.3			
>11.0	76 ± 6.8	76 ± 6.9	72 ± 7.7	75 ± 6.9	76 ± 7.7	75 ± 6.8	79 ± 9.1			
YELLOW POPLAR										
Wood										
5.0-10.9	113 ± 13.5	--	--	115 ± 14.8	109 ± 17.0	113 ± 13.7	112 ± 13.9			
>11.0	101 ± 9.4	100 ± 10.0	98 ± 12.0	100 ± 9.8	111 ± 12.4	100 ± 9.8	111 ± 15.4			
Bark										
5.0-10.9	160 ± 33.1	--	--	140 ± 29.6	196 ± 44.5	162 ± 43.7	271 ± 66.8			
>11.0	115 ± 17.8	104 ± 18.4	99 ± 14.2	103 ± 17.4	160 ± 32.6	105 ± 18.6	190 ± 40.3			
Wood and Bark										
5.0-10.9	120 ± 14.5	--	--	118 ± 15.0	121 ± 17.1	121 ± 16.4	162 ± 22.2			
>11.0	103 ± 8.5	101 ± 9.1	98 ± 10.2	100 ± 8.7	119 ± 11.6	101 ± 9.0	135 ± 18.4			
HARD HARDWOODS										
Wood										
5.0-10.9	62 ± 14.4	--	--	64 ± 15.7	59 ± 11.8	63 ± 15.2	58 ± 10.7			
>11.0	67 ± 14.0	71 ± 15.7	63 i-13.5	70 ± 15.5	59 ± 10.0	70 ± 15.5	60 ± 10.2			
Bark										
5.0-10.9	69 ± 15.1	--	--	64 ± 16.0	72 ± 15.5	66 ± 16.5	81 ± 17.2			
>11.0	65 ± 10.6	62 ± 11.0	60 i-11.8	62 ± 10.7	70 ± 12.3	62 ± 10.5	71 ± 13.8			
Wood and Bark										
5.0-10.9	63 ± 11.7	--	--	64 ± 12.7	62 ± 8.2	64 ± 12.3	66 ± 8.2			
>11.0	67 ± 11.2	69 i-12.9	63 ± 10.5	69 ± 12.7	62 ± 7.2	69 ± 12.9	63 ± 7.7			
WHITE ASH										
Wood										
5.0-10.9	45 ± 2.3	--	--	45 ± 2.5	43 ± 2.3	45 ± 2.5	43 ± 3.0			
>11.0	46 ± 3.0	47 ± 4.1	44 ± 2.7	46 ± 3.2	45 ± 3.3	46 ± 3.2	45 ± 3.8			
Bark										
5.0-10.9	84 ± 19.5	--	--	82 ± 22.1	86 ± 18.5	84 ± 22.8	86 ± 19.0			
>11.0	78 ± 11.2	77 i-11.8	77 i-17.0	77 ± 12.3	80 ± 16.5	77 ± 11.9	78 ± 16.4			

Continued

Table 3.--Average moisture content of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation						Branches		
		Butt to Y-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip				
Percent										
Wood and Bark										
5.0-10.9	51 ± 3.5	--		52 ± 5.2	53 ± 4.8	51 ± 4.4	57 ± b.5			
>11.0	51 ± 3.6	52 ± 4.4	50 ± 5.1	51 ± 3.9	55 ± 6.2	51 ± 3.8	55 ± 6.1			
SWEET BIRCH										
Wood										
5.0-10.9	62 ± 11.3	--		64 ± 11.6	70 ± 2.6	66 ± 8.5	62 ± 5.1			
>11.0	71 ± 4.0	72 ± 4.3	71 ± 2.6	72 ± 3.5	70 ± 3.9	72 ± 3.4	69 ± 7.2			
Bark										
5.0-10.9	66 ± 6.7	--		53 ± 11.1	66 ± 3.3	56 ± 6.8	84 ± 8.0			
>11.0	58 ± 4.7	53 ± 3.9	52 ± 4.1	53 ± 3.9	57 ± 4.5	53 ± 3.8	65 ± 6.4			
Wood and Bark										
5.0-10.9	62 ± 10.3	--		62 ± 11.5	69 ± 2.5	64 ± 8.2	69 ± 5.1			
>11.0	69 ± 3.0	70 ± 3.7	68 ± 2.5	70 ± 3.2	67 ± 2.9	70 ± 3.1	68 ± 3.8			
BLACK LOCUST										
Wood										
5.0-10.9	44 ± 6.5	--		42 ± 8.2	46 ± 3.5	43 ± 6.9	50 ± 6.6			
>11.0	49 ± 10.5	52 ± 12.2	46 ± 10.3	50 ± 11.5	44 ± 7.6	50 ± 11.4	44 ± 6.1			
Bark										
5.0-10.9	57 ± 20.5	--		56 ± 19.4	63 ± 19.2	54 ± 22.Y	67 ± 20.2			
>11.0	55 ± 11.4	57 ± 14.5	54 ± 11.7	56 ± 13.2	57 ± 9.5	56 ± 13.0	56 ± 9.6			
Wood and Bark										
5.0-10.9	46 ± 6.Y	--		45 ± 10.2	51 ± 6.0	45 ± 1.5	57 ± 8.1			
>11.0	50 ± 9.5	53 ± 10.8	48 ± 7.9	51 ± 9.9	48 ± 6.1	51 ± 11.4	48 ± 5.4			
HICKORY										
Wood										
5.0-10.9	51 ± 3.1	--		52 ± 3.5	47 ± 2.8	51 ± 3.4	47 ± 2.5			
>11.0	55 ± 5.5	58 ± 6.6	5% ± 6.2	57 ± 6.4	50 ± 3.Y	57 ± 6.4	50 ± 3.9			
Bark										
5.0-10.9	72 ± 11.1	--		67 ± 9.0	80 ± 14.8	68 ± 9.8	88 ± 15.0			
>11.0	70 ± 11.1	66 ± 10.5	62 ± 10.6	65 ± 10.0	76 ± 115.1	65 ± 10.0	77 ± 15.1			
Wood and Bark										
5.0-10.9	54 ± 3.4	--		54 ± 3.8	55 ± 4.8	54 ± 3.6	61 ± 5.6			
>11.0	58 ± 4.9	59 ± 5.5	54 ± 5.2	58 ± 5.3	58 ± 6.1	58 ± 5.4	59 ± 7.2			

Continued

Table 3.--Average moisture content of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation						Branches		
		Butt to 9-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip				
Percent										
BLACK OAK										
Wood										
5.0-10.9	75 ± 6.7	--								
≥11.0	81 ± 10.7	47 ± 12.7								
			79 ± 10.0							
				JR ± A.4	67 ± 4.1	77 ± 7.8	62 ± 3.1			
				86 ± 12.2	66 ± 6.7	86 ± 17.1	67 ± 7.2			
Bark										
5.0-10.9	69 ± 5.5	--								
≥11.0	67 ± 9.3	57 ± 8.4								
			55 ± R.3							
				61 ± 5.4	75 ± n.4	63 ± 6.2	103 ± 12.6			
				57 ± 8.0	69 ± 11.7	57 ± 5.1	73 ± 15.3			
Wood and Bark										
5.0-10.9	74 ± 4.7	--								
≥11.0	JJ ± 7.8	82 ± 9.8								
			74 ± 7.0							
				75 ± 6.4	68 ± 2.7	75 ± 6.1	76 ± 5.8			
				81 ± 9.6	66 ± 5.3	81 ± 9.7	69 ± 5.1			
CHESTNUT OAK										
Wood										
5.0-10.9	67 ± 3.4	--								
≥11.0	68 ± 4.4	JO ± 4.7								
			62 ± 4.9							
				67 ± 4.3	64 ± 3.1	67 ± 4.0	66 ± 5.5			
				69 ± 4.7	62 ± 4.3	69 ± 4.7	62 ± 4.6			
Bark										
5.0-10.9	53 ± 7.6	--								
≥11.0	59 ± 6.5	58 ± 7.9								
			55 ± 7.7							
				49 ± 6.6	55 ± 9.3	50 ± 6.0	70 ± 14.2			
				58 ± 6.6	63 ± 9.7	58 ± 6.6	64 ± 11.0			
Wood and Bark										
5.0-10.9	64 ± 3.6	--								
≥11.0	66 ± 3.9	67 ± 4.4								
			60 ± 4.5							
				63 ± 4.6	61 ± 3.6	64 ± 3.9	68 ± 5.3			
				67 ± 4.7	62 ± 4.7	67 ± 4.2	63 ± 5.3			
NORTHERN RED OAK										
Wood										
5.0-10.9	79 ± 4.1	--								
≥11.0	81 ± 5.5	86 ± 5.8								
			72 ± 4.7							
				81 ± 4.5	69 ± 3.7	80 ± 4.5	68 ± 3.6			
				84 ± 5.8	68 ± 4.5	84 ± 5.8	69 ± 4.6			
Bark										
5.0-10.9	65 ± 4.7	--								
≥11.0	60 ± 5.6	58 ± 6.0								
			55 ± 4.8							
				64 ± 5.3	67 ± 4.9	64 ± 5.0	71 ± 7.9			
				58 ± 5.7	JO ± 4.4	59 ± 5.7	64 ± 10.4			
Wood and Bark										
5.0-10.9	76 ± 3.6	--								
≥11.0	78 ± 5.0	82 ± 5.6								
			69 ± 4.5							
				79 ± 4.1	69 ± 3.7	78 ± 4.0	69 ± 4.0			
				81 ± 5.5	68 ± 4.3	81 ± 5.5	68 ± 4.5			
SCARLET OAK										
Wood										
5.0-10.9	76 ± 2.9	--								
≥11.0	80 ± 5.3	87 ± 6.0								
			81 ± 6.3							
				80 ± 3.1	71 ± 7.7	80 ± 3.2	64 ± 3.5			
				86 ± 6.0	64 ± 3.9	85 ± 6.1	65 ± 4.0			

Continued

Table 3.--Average moisture content of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation							Branches		
		Butt to Y-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip	Percent				
Bark											
5.0-10.9											
<u>>11.0</u>	71 ± 11.6	63 ± 5.6	60 ± 5.2	60 -- 5.0	63 ± 7.8	72 ± 11.0	64 ± 8.4	87 ± 16.9			
Wood and Bark											
5.0-10.9											
<u>>11.0</u>	75 ± 3.2	77 ± 4.2	83 -- 5.3	78 -- 5.3	77 ± 3.4	71 ± 3.8	77 ± 3.3	72 ± 5.3			
WHITE OAK											
Wood											
5.0-10.9											
<u>>11.0</u>	65 ± 4.3	72 ± 4.8	76 ± 5.8	65 -- 4.1	66 ± 4.6	65 ± 4.5	66 ± 4.5	64 ± 5.0			
Bark											
5.0-10.9											
<u>>11.0</u>	71 ± 7.0	74 ± 5.9	69 -- 8.1	65 -- 7.8	62 ± 5.3	73 ± 9.0	64 ± 5.6	91 ± 10.7			
Wood and Bark											
5.0-10.9											
<u>>11.0</u>	66 ± 4.4	72 ± 3.7	75 ± 4.7	65 -- 3.5	65 ± 4.3	66 ± 4.5	66 ± 4.3	73 ± 5.3			
ALL SPECIES											
Wood											
5.0-10.9											
<u>>11.0</u>	75 ± 25.3	75 ± 19.8	7a -- 19.7	71 -- 20.0	76 ± 25.6	72 ± 74.9	76 ± 25.1	72 ± 26.8			
Bark											
5.0-10.9											
<u>>11.0</u>	81 ± 34.6	73 ± 21.4	69 -- 19.4	66 -- 18.5	74 ± 34.3	88 ± 45.3	78 ± 31.8	105 ± 67.2			
Wood and Bark											
5.0-10.9											
<u>>11.0</u>	75 ± 24.0	74 ± 18.1	76 -- 17.8	70 -- 17.6	76 ± 23.7	74 ± 23.8	76 ± 24.5	83 ± 34.3			
					76 ± 17.5	73 ± 22.5	76 ± 17.9	77 ± 28.5			

Table 4. -- Average proportion of wood and bark green weight in bark, by tree component and size class, for hardwood species in the Southern Appalachian Mountains

Tree size class (inches)	Total tree	Average and standard deviation						Branches		
		Butt to 9-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip				
Percent										
SOFT HARDWOODS										
5.0-10.9	18 ± 3.1	--	--	15 ± 2.8	20 ± 4.6	16 ± 2.8	31 ± 6.2			
>11.0	17 ± 2.4	13 ± 3.0	18 ± 4.1	14 ± 2.8	22 ± 6.7	15 ± 2.8	30 ± 5.0			
BASSWOOD										
5.0-10.9	22 ± 2.3	--	--	18 ± 2.1	27 ± 3.4	19 ± 2.4	39 ± 4.6			
>11.0	19 ± 2.1	14 ± 1.6	19 ± 1.4	15 ± 1.7	29 ± 1.9	15 ± 1.7	36 ± 4.1			
BLACKGUM										
5.0-10.9	18 ± 1.1	--	--	15 ± 1.5	22 ± 3.6	16 ± 1.4	26 ± 3.3			
>11.0	16 ± 4.5	13 ± 5.1	16 ± 5.3	14 ± 5.0	23 ± 5.4	14 ± 5.0	25 ± 4.0			
RED MAPLE										
5.0-10.9	16 ± 2.1	--	--	12 ± 2.1	18 ± 3.2	13 ± 2.4	27 ± 4.4			
>11.0	15 ± 1.0	11 ± 1.7	17 ± 4.9	11 ± 1.6	22 ± 3.5	11 ± 1.6	27 ± 3.3			
YELLOW POPLAR										
5.0-10.9	19 ± 2.6	--	--	16 ± 2.1	17 ± 2.4	16 ± 1.9	33 ± 4.2			
>11.0	17 ± 1.7	14 ± 1.6	20 ± 2.8	15 ± 1.7	19 ± 7.0	15 ± 1.7	31 ± 3.9			
HARD HARDWOODS										
5.0-10.9	18 ± 3.3	--	--	15 ± 3.5	22 ± 5.1	16 ± 3.6	29 ± 5.2			
>11.0	17 ± 2.8	13 ± 2.5	18 ± 4.6	14 ± 2.6	26 ± 8.9	14 ± 2.6	27 ± 4.5			
WHITE ASH										
5.0-10.9	18 ± 3.5	--	--	15 ± 3.3	25 ± 6.2	15 ± 3.5	32 ± 4.5			
>11.0	16 ± 2.2	12 ± 1.9	18 ± 3.8	13 ± 1.9	30 ± 6.6	13 ± 2.0	30 ± 3.9			
SWEET BIRCH										
5.0-10.9	18 ± 1.2	--	--	12 ± 1.4	19 ± 2.3	13 ± 1.4	33 ± 3.0			
>11.0	18 ± 3.0	14 ± 2.6	17 ± 4.2	14 ± 2.8	22 ± 4.3	14 ± 2.8	28 ± 5.1			
BLACK LOCUST										
5.0-10.9	16 ± 4.9	--	--	13 ± 5.6	19 ± 5.4	14 ± 5.5	25 ± 4.2			
>11.0	15 ± 1.9	12 ± 1.4	16 ± 2.1	13 ± 1.4	24 ± 3.3	13 ± 1.5	25 ± 4.5			
HICKORY										
5.0-10.9	19 ± 2.9	--	--	16 ± 3.0	24 ± 5.1	17 ± 3.5	32 ± 5.7			
>11.0	18 ± 3.0	13 ± 2.6	17 ± 3.6	14 ± 2.6	32 ± 8.6	14 ± 2.6	28 ± 4.2			

Continued

Table 4.--Average proportion of wood and bark green weight in bark, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation						Branches
		Butt to 9-inch top		9-inch to 4-inch top	Stem		4-inch to tip	
		Percent	Percent	4-inch top	4-inch top	tip	tip	
BLACK OAK								
5.0-10.9	19 ± 2.3				17 ± 2.3	24 ± 2.4	18 ± 2.4	31 ± 2.7
≥11.0	18 ± 2.1	14 --	14 ± 2.1	18 ± 2.4	15 ± 2.1	27 ± 3.6	15 ± 2.0	28 ± 2.6
CHESTNUT OAK								
5.0-10.9	21 ± 3.5				19 ± 3.7	27 ± 4.8	20 ± 3.5	31 ± 7.0
≥11.0	20 ± 2.7	16 --	16 ± 2.6	24 ± 5.1	17 ± 2.7	34 ± a.4	17 ± 2.7	31 ± 3.6
NORTHERN RED OAK								
5.0-10.9	16 ± 1.3				14 ± 1.2	19 ± 2.3	14 ± 1.3	25 ± 2.1
≥11.0	15 ± 1.3	12 --	12 ± 1.4	16 ± 2.8	12 ± 1.3	15 ± 2.0	12 ± 1.3	23 ± 2.1
SCARLET OAK								
5.0-10.9	20 ± 2.8				26 ± 2.1	22 ± 1.6	17 ± 2.1	29 ± 2.2
≥11.0	15 ± 1.1	12 --	12 ± 1.1	15 ± 1.8	12 ± 1.2	22 ± 2.8	13 ± 1.2	24 ± 2.8
WHITE OAK								
5.0-10.9	16 ± 2.6				12 ± 2.2	22 ± 3.5	13 ± 2.0	30 ± 2.6
≥11.0	16 ± 2.0	12 --	12 ± 1.8	18 ± 3.8	12 ± 1.8	29 ± 7.0	12 ± 1.8	26 ± 3.8
ALL SPECIES								
5.0-10.9	18 ± 3.2	--			15 ± 3.3	22 ± 5.1	16 ± 3.4	30 ± 5.6
≥11.0	17 ± 2.7	13 ± 2.6	13 ± 2.6	18 ± 4.5	14 ± 2.6	25 ± 8.7	14 ± 2.6	28 ± 4.8

Table 5.--Average green weight per cubic foot of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains

Tree size class (inches)	Total tree	Average and standard deviation						Branches		
		Butt to 9-inch top	9-inch to 4-inch top	Butt to cl-inch top	4-inch to tip	Butt to tip				
- - - - - Pounds per cubic foot - - - - -										
SOFT HARDWOODS										
Wood										
5.0-10.9	56 ± 6.3	--		56 ± 6.2		56 ± 1.4		56 ± 6.2		
>11.0	54 ± 5.1	55 ± 5.5	55 ± 5.3	53 ± 5.1'		58 ± 8.6	53 ± 5.1	57 ± 6.3		
Bark										
5.0-10.9	55 ± 6.0	--		54 ± 7.4		57 ± 6.6		53 ± 7.0		
>11.0	48 ± 6.3	48 ± 7.2	50 ± 8.3	46 ± 7.3		54 ± 5.6	46 ± 7.3	56 ± 5.7		
Wood and Bark										
5.0-10.9	55 ± 4.7	--		55 ± 4.11		54 ± 5.3		55 ± 4.8		
>11.0	53 ± 4.4	54 ± 4.7	54 ± 4.3	32 ± 4.6		54 ± 5.3	52 ± 4.6	57 ± 4.5		
BASSWOOD										
Wood										
5.0-10.9	51 ± 1.5	--		53 ± 1.8		46 ± 3.1		52 ± 1.7		
>11.0	49 ± 3.1	50 ± 4.2	49 ± 2.1	50 ± 3.13		46 ± 3.0	49 ± 3.7	41 ± 2.6		
Bark										
5.0-10.9	51 ± 2.4	--		50 ± 2.5		52 ± 3.2		50 ± 2.4		
>11.0	50 ± 1.5	49 ± 2.1	48 ± 2.7	48 ± 2.7		51 ± 2.2	49 ± 2.6	54 ± 2.0		
Wood and Bark										
5.0-10.9	51 ± 1.1	--		52 ± 1.3		47 ± 2.1		52 ± 1.2		
>11.0	49 ± 3.2	49 ± 3.8	48 ± 1.5	49 ± 3.3		47 ± 2.0	49 ± 3.3	50 ± 3.3		
BLACKGUM										
Wood										
5.0-10.9	67 ± 4.0	--		66 ± 5.0		64 ± 3.2		66 ± 4.7		
>11.0	61 ± 5.6	60 ± 6.4	60 ± 4.3	60 ± 6.0		62 ± 5.0	60 ± 6.0	65 ± 3.8		
Bark										
5.0-10.9	45 ± 2.4	--		42 ± 2.3		45 ± 2.1		42 ± 2.2		
>11.0	42 ± 3.6	40 ± 4.8	40 ± 6.6	40 ± 5.1		46 ± 4.1	40 ± 4.9	45 ± 2.9		
Wood and Bark										
5.0-10.9	61 ± 3.3	--		61 ± 4.0		59 ± 2.9		61 ± 3.7		
>11.0	57 ± 4.5	57 ± 5.4	55 ± 3.7	57 ± 5.0		58 ± 4.0	57 ± 5.0	63 ± 2.7		
RED MAPLE										
Wood										
5.0-10.9	58 ± 2.7	--		59 ± 2.7		55 ± 3.1		58 ± 2.8		
>11.0	57 ± 2.5	57 ± 2.9	55 ± 4.1	57 ± 2.6		54 ± 3.1	57 ± 2.6	56 ± 3.0		

Continued

Table 5.--Average green weight per cubic foot of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation						Branches		
		Butt to 9-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip				
- - - - - Pounds per cubic foot - - - - -										
Bark										
5.0-10.9	60 ± 3.3	--		61 ± 4.4	61 ± 3.2	61 ± 4.0	58 ± 3.5			
≥11.0	58 ± 4.2	58 ± 5.0	59 ± 7.5	58 ± 5.2	60 ± 3.2	58 ± 5.1	57 ± 5.3			
Wood and Bark										
5.0-10.9	58 ± 2.4	--		59 ± 2.7	56 ± 2.8	58 ± 2.6	56 ± 3.6			
≥11.0	57 ± 2.3	57 ± 2.7	55 ± 3.8	57 ± 2.5	55 ± 2.6	57 ± 2.4	57 ± 3.1			
YELLOW POPLAR										
Wood										
5.0-10.9	51 ± 3.7	--		52 ± 3.7	57 ± 7.6	52 ± 4.3	54 ± 3.7			
≥11.0	52 ± 3.7	53 ± 3.1	57 ± 4.2	52 ± 3.6	62 ± 12.9	52 ± 3.1	58 ± 5.3			
Bark										
5.0-10.9	56 ± 4.0	--		55 ± 4.6	59 ± 3.5	52 ± 3.7	59 ± 3.7			
≥11.0	46 ± 4.1	46 ± 2.5	51 ± 3.4	43 ± 4.1	54 ± 4.3	43 ± 4.2	59 ± 3.3			
Wood and Bark										
5.0-10.9	52 ± 3.4	--		52 ± 3.4	52 ± 5.4	52 ± 3.6	56 ± 3.0			
≥11.0	51 ± 3.4	52 ± 2.6	56 ± 3.6	50 ± 3.3	55 ± 5.3	50 ± 3.4	58 ± 4.1			
HARD HARDWOODS										
Wood										
5.0-10.9	62 ± 5.9	--		62 ± 6.4	61 ± 9.7	62 ± 6.4	60 ± 4.7			
≥11.0	62 ± 4.5	63 ± 4.9	63 ± 5.5	63 ± 4.8	60 ± 5.5	63 ± 4.8	62 ± 4.2			
Bark										
5.0-10.9	53 ± 9.3	--		53 ± 11.0	54 ± 8.8	53 ± 10.7	53 ± 7.2			
≥11.0	55 ± 8.6	55 ± 9.8	56 ± 9.4	55 ± 9.7	56 ± 7.6	55 ± 9.6	54 ± 7.5			
Wood and Bark										
5.0-10.9	60 ± 5.9	--		60 ± 6.6	59 ± 7.6	60 ± 6.5	57 ± 4.5			
≥11.0	61 ± 5.0	61 ± 5.3	61 ± 5.9	61 ± 5.3	59 ± 5.2	61 ± 5.2	59 ± 4.9			
WHITE ASH										
Wood										
5.0-10.9	53 ± 2.7	--		53 ± 3.0	54 ± 5.4	53 ± 3.1	53 ± 2.2			
≥11.0	52 ± 3.2	52 ± 3.8	55 ± 6.4	52 ± 3.6	58 ± 9.2	52 ± 3.6	54 ± 3.4			
Bark										
5.0-10.9	46 ± 5.3	--		43 ± 5.2	51 ± 4.9	44 ± 5.4	53 ± 4.8			
≥11.0	45 ± 5.4	42 ± 5.1	45 ± 5.8	42 ± 5.0	49 ± 6.5	43 ± 5.0	49 ± 7.1			

Continued

Table 5.--Average green weight per cubic foot of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation							
		Butt to 9-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip	Branches		
- - - - - Pounds per cubic foot - - - - -									
Wood and Bark									
5.0-10.9	52 ± 2.7	--		51 ± 2.9	53 ± 4.9	51 ± 3.1	53 ± 2.0		
>11.0	51 ± 2.8	50 ± 3.2	53 ± 5.1	50 ± 2.9	55 ± 7.7	50 ± 3.0	52 ± 4.0		
SWEET BIRCH									
Wood									
5.0-10.9	60 ± 1.7	--		60 ± 2.6	63 ± 1.6	61 ± 2.4	58 ± 3.1		
>11.0	63 ± 3.2	63 ± 3.7	64 ± 3.1	63 ± 3.3	63 ± 3.2	63 ± 3.3	63 ± 3.7		
Bark									
5.0-10.9	62 ± 1.9	--		68 ± 1.1	65 ± 2.4	67 ± 1.1	58 ± 2.4		
>11.0	b4 ± 1.7	68 ± 1.5	68 ± 2.4	69 ± 1.5	66 ± 1.9	68 ± 1.5	60 ± 2.7		
Wood and Bark									
5.0-10.9	60 ± 1.2	--		61 ± 2.3	64 ± 1.2	62 ± 2.1	58 ± 2.3		
>11.0	63 ± 2.8	64 ± 3.3	65 ± 2.6	64 ± 2.9	63 ± 2.6	64 ± 2.8	62 ± 3.4		
BLACK LOCUST									
Wood									
5.0-10.9	59 ± 4.5	--		59 ± 5.5	58 ± 4.5	59 ± 5.1	58 ± 2.2		
>11.0	60 ± 2.9	60 ± 3.2	60 ± 3.6	60 ± 2.9	62 ± 4.3	60 ± 2.9	60 ± 2.7		
Bark									
5.0-10.9	30 ± 3.2	--		29 ± 4.0	33 ± 3.5	29 ± 3.8	34 ± 4.8		
>11.0	29 ± 2.5	28 ± 2.4	30 ± 3.0	28 ± 2.6	34 ± 2.4	28 ± 2.6	33 ± 2.7		
Wood and Bark									
5.0-10.9	51 ± 3.7	--		52 ± 4.9	51 ± 3.4	52 ± 4.6	49 ± 2.4		
>11.0	52 ± 2.4	52 ± 2.7	52 ± 2.9	52 ± 2.5	52 ± 3.8	52 ± 2.5	49 ± 2.3		
HICKORY									
Wood									
5.0-10.9	67 ± 6.7	--		68 ± 7.0	74 ± 18.8	68 ± 7.9	59 ± 4.6		
>11.0	62 ± 2.0	63 ± 2.7	65 ± 5.0	63 ± 2.3	63 ± 7.0	63 ± 2.3	60 ± 2.7		
Bark									
5.0-10.9	53 ± 2.1	--		54 ± 1.7	55 ± 2.9	54 ± 1.7	52 ± 4.6		
>11.0	56 ± 1.9	57 ± 2.1	57 ± 2.1	57 ± 2.0	57 ± 3.0	57 ± 2.0	54 ± 3.0		
Wood and Bark									
5.0-10.9	64 ± 5.3	--		65 ± 5.9	68 ± 13.2	66 ± 6.5	56 ± 3.7		
>11.0	61 ± 1.8	62 ± 2.4	63 ± 3.9	62 ± 2.1	61 ± 5.2	62 ± 2.0	58 ± 2.2		

Continued

Table 5.--Average green weight per cubic foot of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation							
		Butt to 9-inch top	9-inch to 4-inch top	Stem	Butt to 4-inch top	4-inch to tip	Butt to tip	Branches	
- - - - - Pounds per cubic foot - - - - -									
BLACK OAK									
Wood									
5.0-10.9	62 ± 3.1	--		62 ± 3.7		62 ± 3.3	62 ± 3.3	63 ± 2.1	
≥11.0	63 ± 1.8	63 ± 2.1		63 12.2		57 ± 4.5	63 ± 2.1	64 ± 1.6	
Bark									
5.0-10.9	56 ± 3.0	--		56 ± 3.5		58 ± 3.4	56 ± 3.4	54 ± 5.3	
≥11.0	57 ± 2.6	57 ± 2.9		57 ± 2.8		59 ± 3.3	57 ± 2.7	57 ± 3.5	
Wood and Bark									
5.0-10.9	61 ± 2.7	--		61 ± 3.2		61 ± 2.5	61 ± 2.9	60 ± 2.5	
≥11.0	62 ± 1.7	62 ± 2.1		62 ± 3.0		58 ± 3.4	62 ± 2.1	62 ± 1.6	
CHESTNUT OAK									
Wood									
5.0-10.9	62 ± 4.0	--		63 ± 5.0		60 ± 3.1	63 ± 4.3	61 ± 2.0	
≥11.0	64 ± 2.4	65 ± 2.5		65 ± 2.6		57 ± 3.9	64 ± 2.6	63 ± 3.0	
Bark									
5.0-10.9	48 ± 5.2	--		47 ± 5.3		47 ± 4.9	47 ± 5.2	50 ± 4.9	
≥11.0	50 ± 3.7	51 ± 4.0		51 ± 3.9		50 ± 3.8	51 ± 3.9	50 ± 3.9	
Wood and Bark									
5.0-10.9	59 ± 4.2	--		59 ± 5.1		56 ± 3.4	59 ± 4.5	57 ± 2.7	
≥11.0	61 ± 2.6	62 ± 2.7		62 ± 2.7		55 ± 3.1	62 ± 2.7	5X ± 3.2	
NORTHERN RED OAK									
Wood									
5.0-10.9	65 ± 1.9	--		65 ± 1.8		61 ± 2.7	65 ± 2.0	63 ± 2.2	
≥11.0	65 ± 1.2	66 ± 1.5		66 ± 1.8		62 ± 1.6	66 ± 1.5	64 ± 1.8	
Bark									
5.0-10.9	63 ± 2.0	--		64 ± 2.1		63 ± 3.2	64 ± 2.2	60 ± 2.4	
≥11.0	62 ± 1.9	63 ± 2.5		63 ± 2.4		62 ± 2.0	63 ± 2.4	61 ± 2.8	
Wood and Bark									
5.0-10.9	64 ± 1.7	--		65 ± 1.6		61 ± 2.5	65 ± 1.8	62 ± 2.0	
≥11.0	65 ± 1.1	65 ± 1.5		65 ± 1.4		62 ± 1.3	65 ± 1.4	63 ± 1.7	

Continued

Table 5.--Average green weight per cubic foot of wood, bark, and wood and bark combined, by tree component and size class, for hardwood species in the Southern Appalachian Mountains--Continued

Tree size class (inches)	Total tree	Average and standard deviation						Branches		
		Stem								
		Butt to 9-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip				
I										
-- Pounds per cubic foot --										
SCARLET OAK										
Wood										
5.0-10.9	65 ± 1.8	--		66 ± 2.4	62 ± 1.9	65 ± 2.1	63 ± 1.7			
>11.0	65 ± 1.5	64 ± 1.7	67 ± 3.5	65 ± 1.7	61 ± 2.8	64 ± 1.7	65 ± 2.0			
Bark										
5.0-10.9	58 ± 2.3	--		60 ± 2.0	59 ± 2.9	60 ± 1.8	54 ± 4.2			
>11.0	62 ± 2.5	63 ± 2.3	64 ± 2.0	63 ± 2.2	60 ± 2.7	63 ± 2.2	60 ± 3.4			
Wood and Bark										
5.0-10.9	63 ± 1.8	--		65 ± 2.3	61 ± 1.8	64 ± 2.0	60 ± 1.9			
>11.0	64 ± 1.3	64 ± 1.4	67 ± 3.1	64 ± 1.5	61 ± 2.3	64 ± 1.4	63 ± 1.7			
WHITE OAK										
Wood										
5.0-10.9	65 ± 1.8	--		65 ± 2.2	63 ± 2.3	65 ± 1.9	63 ± 2.3			
>11.0	65 ± 1.7	65 ± 1.7	64 ± 5.6	65 ± 1.6	61 ± 3.1	65 ± 1.6	65 ± 2.8			
Bark										
5.0-10.9	51 ± 3.3	--		50 ± 3.7	52 ± 3.2	50 ± 3.6	53 ± 2.5			
>11.0	56 ± 2.7	56 ± 3.9	57 ± 2.7	56 ± 3.6	57 ± 2.1	56 ± 3.5	55 ± 2.8			
Wood and Bark										
5.0-10.9	62 ± 1.7	--		63 ± 2.0	60 ± 2.2	63 ± 1.8	60 ± 2.2			
>11.0	63 ± 1.7	64 ± 1.5	62 ± 4.5	64 ± 1.6	60 ± 2.4	64 ± 1.6	62 ± 2.5			
ALL SPECIES										
Wood										
5.0-10.9	60 ± 6.6	--		60 ± 6.9	60 ± 9.4	60 ± 6.9	58 ± 5.7			
>11.0	60 ± 6.0	61 ± 5.9	62 ± 6.2	60 ± 6.3	60 ± 1.5	60 ± 6.2	61 ± 5.2			
Bark										
5.0-10.Y	53 ± 8.5	--		53 ± 10.0	55 ± a.2	53 ± 9.7	54 ± b.?			
>11.0	53 ± 8.6	54 ± 9.7	55 ± 9.4	53 ± 9.9	55 ± 1.2	53 ± 9.9	55 ± 7.1			
Wood and Bark										
5.0-10.9	58 ± 6.0	--		59 ± 6.5	58 ± 7.5	59 ± 6.5	57 ± 4.6			
>11.0	59 ± 6.0	60 ± 6.0	60 ± 6.3	59 ± 6.5	58 ± 5.5	59 ± 6.4	59 ± 4.9			

Table 6. --Average green weight of wood and bark per cubic foot of wood, by tree component and size class, for hardwood species in the Southern Appalachian Mountains

Tree size class finches)	Total tree	Average and standard deviation						Branches		
		Stem								
		Butt to 9-inch top	9-inch to 4-inch top	Butt to 4-inch top	4-inch to tip	Butt to tip				
- - - - - Pounds per cubic foot - - - - -										
SOFT HARDWOODS										
5.0-10.9 ≥11.0	68 ± 7.5	--	63 ± 5.4	68 ± 6.4	66 ± 7.7	69 ± 9.1	66 ± 7.3	81 ± 8.3		
5.0-10.9 ≥11.0	65 ± 5.5	63 ± 5.4		68 ± 6.4	62 ± 5.1	73 ± 8.4	63 ± 5.1	82 ± 6.6		
BASSWOOD										
5.0-10.9 ≥11.0	66 ± 1.5		58 i-5.1	60 ± 2.6	65 ± 2.3	63 ± 3.3	65 ± 2.2	78 ± 7.6		
5.0-10.9 ≥11.0	61 ± 4.5			58 ± 2.6	58 ± 4.6	64 ± 3.3	58 ± 4.6	75 ± 6.9		
BLACKGUM										
5.0-10.9 ≥11.0	81 ± 4.0		70 i-4.6	71 ± 1.7	78 ± 5.0	82 ± 1.9	78 ± 4.9	92 ± 4.0		
5.0-10.9 ≥11.0	73 ± 4.6			70 ± 1.7	70 ± 4.2	81 ± 2.4	70 ± 4.1	86 ± 5.5		
RED MAPLE										
5.0-10.9 ≥11.0	69 ± 4.1		64 i-3.3	66 i-4.5	67 ± 4.2	68 ± 5.0	67 ± 4.3	78 ± 9.6		
5.0-10.9 ≥11.0	67 ± 3.4			64 ± 3.3	64 ± 3.1	69 ± 4.0	64 ± 3.1	77 ± 3.1		
YELLOW POPLAR										
5.0-10.9 ≥11.0	63 ± 5.6		61 ± 7.9	--	61 ± 5.2	67 ± 10.0	62 ± 5.6	81 ± 4.4		
5.0-10.9 ≥11.0	63 ± 4.3			72 ± 6.3	61 ± 4.0	75 ± 8.5	61 ± 4.1	83 ± 5.8		
HARD HARDWOODS										
5.0-10.9 ≥11.0	75 ± 7.3		72 ± 5.9	--	73 ± 7.5	78 ± 7.6	74 ± 7.8	85 ± 7.1		
5.0-10.9 ≥11.0	75 ± 5.8			77 ± 6.7	72 ± 5.7	82 ± 9.0	73 ± 5.7	85 ± 6.7		
WHITE ASH										
5.0-10.9 ≥11.0	65 ± 4.0		59 ± 3.8	67 ± 6.8	62 ± 3.7	7% ± 6.2	63 ± 4.n	77 ± 5.4		
5.0-10.9 ≥11.0	63 ± 3.9			67 ± 6.8	60 ± 3.8	R2 ± 9.5	60 ± 3.8	75 ± 6.0		
SWEET BIRCH										
5.0-10.9 ≥11.0	74 ± 2.2	--	73 ± 4.1	77 ± 3.4	69 ± 2.5	78 ± 1.3	70 ± 2.5	86 ± 6.0		
5.0-10.9 ≥11.0	77 ± 3.4			77 ± 3.4	73 ± 3.6	80 ± 4.1	73 ± 3.5	88 ± 6.3		
BLACK LOCUST										
5.0-10.9 ≥11.0	70 ± 3.3		68 ± 3.4	71 ± 4.1	68 ± 4.7	71 ± 3.0	69 ± 3.8	78 ± 4.5		
5.0-10.9 ≥11.0	70 ± 2.6			69 ± 4.1	69 ± 2.8	82 ± 4.3	69 ± 2.8	79 ± 4.6		
HICKORY										
5.0-10.9 ≥11.0	83 ± 8.0	--	73 ± 2.7	--	81 ± 7.4	87 ± 10.5	82 ± 9.1	86 ± 5.6		
5.0-10.9 ≥11.0	76 ± 2.9			7R ± 6.5	73 ± 2.5	91 ± 8.1	73 ± 2.5	86 ± 5.7		

Continued

Table 6...Average green weight of wood and bark per cubic foot of wood, by tree component and size class, for hardwood species in the Southern Appalachian Mountains

Tree size class (inches)	Total tree	Average and standard deviation						
		Butt to 9-inch top		9-inch to 4-inch top		Butt to 4-inch top		4-inch to tip
		Pounds	per cubic foot	Branches				
BLACK OAK								
5.0-10.9	77 ± 2.5	--			75 ± 3.3	81 ± 3.6	76 ± 2.9	91 ± 4.5
≥11.0	77 ± 2.4	74 ± 2.3		80 ± 3.0	74 ± 2.2	79 ± 4.2	74 ± 2.1	88 ± 3.9
CHESTNUT OAK								
5.0-10.9	79 ± 5.0				78 ± 5.0	82 ± 5.8	78 ± 4.8	89 ± 9.0
≥11.0	80 ± 3.4	77 ± 2.8		81 ± 6.6	78 ± 3.1	86 ± 8.9	78 ± 3.1	91 ± 4.8
NORTHERN RED OAK								
5.0-10.9	77 ± 2.0	--			76 ± 2.0	75 ± 3.0	75 ± 2.0	83 ± 3.5
≥11.0	77 ± 1.8	75 ± 1.8		78 ± 3.2	75 ± 1.8	72 ± 1.6	75 ± 1.8	a4 ± 3.0
SCARLET OAK								
5.0-10.9	a1 ± 2.5	--			78 ± 2.6	79 ± 1.7	78 ± 2.2	90 ± 3.7
≥11.0	76 ± 1.9	73 ± 2.1		79 ± 3.5	74 ± 2.1	78 ± 3.4	74 ± 2.1	85 ± 3.7
WHITE OAK								
5.0-10.9	77 ± 3.4	--			74 ± 2.7	al ± 3.3	75 ± 2.8	91 ± 3.8
≥11.0	78 ± 2.2	74 ± 1.9		78 ± 5.2	74 ± 1.8	88 ± 7.0	74 ± 1.8	88 ± 5.4
ALL SPECIES								
5.0-10.Y	73 ± 8.0	--			71 ± 8.1	75 ± 9.0	72 ± a.3	84 ± 7.6
≥11.0	73 ± 7.2	70 ± 6.8		75 ± 7.6	70 ± 7.1	80 ± 9.6	70 ± 7.1	a4 ± 6.8

Table 7.--Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. as the independent variable

Species or species group	Weight green or dry	Regression equation coefficients				Coefficient of determination (R ²)	Standard error ³ (S _{y.x})	No. of trees sampled
		Trees <11.0 in d.b.h. ¹	b	a''	b			
TOTAL-TREE WOOD AND BARK								
Soft Hardwoods	Green	3. 55211	1. 25948	4.02745	1.23329	0.98	0.0642	128
	Dry	1. 56282	1. 28807	1.88621	1.24885	0.97	0.0758	128
Basswood	Green	3. 71029	1. 74226	5.02472	1.17902	0.98	0.0552	18
	Dry	1. 94274	1. 21008	1.47600	1.26737	0.98	0.0630	18
Blackgum (upland)	Green	3.32017	1. 25136	4.90406	1.17002	0.98	0.0619	18
	Dry	1. 54160	1. 27590	2.01627	1.21993	0.97	0.0679	18
Red maple	Green	4.02365	1. 25353	10.63281	1.05091	0.98	0.0602	30
	Dry	2. 02338	1. 27612	5.2879"	1.07581	n.98	U.0558	30
Yellow-poplar	Green	2. 53157	1. 33741	4.17992	1.23285	0.99	0.0581	62
	Dry	0.87948	1.40401	1.65215	1.27254	n.99	0.0568	62
Hard Hardwoods	Green	3. 20171	1. 30631	3.74095	1.27386	0.97	0.0794	347
	Dry	1.99067	1. 30291	2.66968	1.24172	0.97	n.0738	347
White ash	Green	4. 26515	1.21919	5.51740	1.16551	n.98	0.0617	52
	Dry	2. 71163	1.22990	3.96491	1.15068	0.98	0.0633	52
Sweet birch	Green	7. 26568	1.14114	6.22976	1.17321	0.99	0.0419	21
	Dry	4. 29408	1.14203	3.80734	1.16711	0.99	0.0418	21
Black locust	Green	6. 12062	1.08931	1.36924	1.40154	0.96	0.0780	18
	Dry	4. 13741	1.08876	1.04649	1.37539	0.95	0.0831	18
Hickory	Green	1. 37649	1.50566	4.68499	1.25027	0.99	0.0595	54
	Dry	0. 93747	1.49389	3.30276	1.23130	0.98	0.0637	54
Black oak	Green	2. 21828	1.36803	3.65717	1.26378	0.99	0.0556	27
	Dry	1. 29270	1.36723	2.54650	1.22586	0.98	0.0607	27
Chestnut oak	Green	1. 34863	1.48845	5.41481	1.19861	0.98	0.0690	51
	Dry	0. 86674	1.47585	3.40602	1.19049	0.98	0.0667	51
North. red oak	Green	5.08421	1.23759	5.81355	1.70964	0.99	0. n452	71
	Dry	3.06739	1.22338	3.28071	1.20936	0.99	0.0488	71
Scarlet oak	Green	2. 81706	1.34308	4. 69089	1.23675	0.99	0.0444	27
	Dry	1. 62952	1.34103	2.94915	1.21733	0.99	0.0481	27
White oak	Green	2. 82506	1.34053	2.51286	1.36495	0.99	0.0566	28
	Dry	1. 73738	1.33404	1.69511	1.33917	0.99	0.0594	28
All Species	Green	3. 29754	1.29311	3.65829	1.27146	0.97	0.0790	475
	Dry	1. 83051	1.30348	2.24309	1.26110	0.96	0.0948	475

Continued

Table 7--Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. as the independent variable--Continued

Species or species group	Weight green or dry	Regression equation		coefficients		Coefficient of determination (R^2)	standard error ³ ($S_{y,x}$)	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹	Trees > 11.0 in d.b.h. ²	a'	b			
TOTAL-TREE WOOD								
Soft Hardwoods	Green	2.65877	1.28067	3.26758	1.23767	0.98	0.0681	128
	Dry	1.20522	1.30165	1.45172	1.26285	0.97	0.0854	128
Basswood	Green	2.58221	1.26827	3.14665	1.22705	0.98	0.0551	18
	Dry	1.26050	1.24541	0.86609	1.32366	0.97	0.0670	18
Blackgum (upland)	Green	2.55358	1.26884	4.23002	1.16360	0.97	0.0724	18
	Dry	1.14382	1.28857	1.50453	1.23141	0.96	0.0888	18
Red maple	Green	3.05121	1.27840	9.88085	1.03339	0.97	0.0597	30
	Dry	1.45160	1.31226	5.01312	1.05382	0.98	0.0557	30
Yellow-poplar	Green	1.86103	1.36142	3.33413	1.23984	0.99	0.0592	62
	Dry	0.74867	1.40085	1.36501	1.27561	0.99	0.0585	62
Hard Hardwoods	Green	2.16129	1.33180	3.11979	1.27371	0.97	0.0834	347
	Dry	1.51263	1.32307	2.34759	1.23142	0.97	0.0790	347
White ash	Green	2.87027	1.26533	4.70464	1.16229	0.98	0.0612	52
	Dry	2.07306	1.25505	3.41697	1.15086	0.98	0.0637	52
Sweet birch	Green	5.91898	1.14179	4.85269	1.18321	0.98	0.0507	21
	Dry	3.66009	1.13191	3.11384	1.16562	0.98	0.0510	21
Black locust	Green	5.20919	1.08668	0.95293	1.44088	0.95	0.0864	18
	Dry	3.59150	1.08426	0.77942	1.40281	0.95	0.0855	18
Hickory	Green	0.97960	1.53720	3.93165	1.24743	0.98	0.0660	54
	Dry	0.69361	1.52150	2.90230	1.22305	0.98	0.0708	54
Black oak	Green	1.45544	1.41790	3.38847	1.24169	0.98	0.05911	27
	Dry	0.85607	1.41438	2.64971	1.17879	0.98	0.0660	27
Chestnut oak	Green	1.02336	1.49892	4.11244	1.20889	0.98	0.0693	51
	Dry	0.62578	1.49459	2.57329	1.19976	0.98	0.0688	51
North. red oak	Green	3.94331	1.25731	4.95616	1.20964	0.99	0.0463	71
	Dry	2.36123	1.74202	2.86474	1.20171	0.99	0.0499	71
Scarlet oak	Green	1.80365	1.39869	3.70487	1.24859	0.99	0.0443	27
	Dry	1.10376	1.38254	2.36997	1.77311	0.99	0.0497	27
White oak	Green	2.47774	1.33511	2.07560	1.36779	0.99	0.0578	28
	Dry	1.48789	1.33079	1.45208	1.33587	0.99	0.0617	28
All Species	Green	7.44774	1.31733	3.02592	1.27269	0.97	0.0829	475
	Dry	1.39612	1.32195	1.90236	1.25744	0.95	0.1003	475

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2)b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2)b$$

Where: **Y** = component weight in pounds

D = tree d.b.h. in inches

a', **a''**, **b** = regression coefficients

³ \log_{10} form

Table S.--Regression equations for estimating green and dry weight of the total-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. as the independent variable

Species or species group	Weight green or dry	Regression equation coefficients				Coefficient of determination (R^2)	Standard errors ($S_{y,x}$)	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹	b	a" ²	b			
TOTAL-STEM WOOD AND BARK								
Soft Hardwoods	Green	3.22563	1.23876	2.88886	1.26175	0.97	0.0785	128
	Dry	1.40805	1.27033	1.34203	1.28034	0.97	0.0801	128
Basswood	Green	3.34246	1.22154	5.22567	1.12836	0.98	0.0485	18
	Dry	1.74995	1.19103	1.49368	1.22405	0.98	0.0575	18
Blackgum (upland)	Green	1.64629	1.34504	3.43542	1.19165	0.97	0.0727	18
	Dry	0.77244	1.36853	1.40359	1.24400	0.97	0.0790	18
Red maple	Green	4.94211	1.14841	6.87118	1.07970	0.97	0.0679	30
	Dry	2.41282	1.17937	3.56511	1.09796	0.97	0.0631	30
Yellow-poplar	Green	2.18263	1.34804	4.43647	1.20013	0.98	0.0596	62
	Dry	0.76237	1.41643	1.76476	1.24142	0.99	0.0599	62
Hard Hardwoods	Green	3.09026	1.27061	4.67860	1.18413	0.97	0.0776	347
	Dry	1.93666	1.26546	3.53278	1.14011	0.97	0.0730	347
White ash	Green	4.84664	1.13887	3.97350	1.18029	0.97	0.0682	52
	Dry	3.12185	1.14771	2.84169	1.16732	0.97	0.0704	52
Sweet birch	Green	5.76494	1.12244	4.79623	1.16080	0.98	0.0521	21
	Dry	3.34713	1.27356	3.06473	1.14574	0.98	0.0511	21
Black locust	Green	5.82355	1.05973	0.89294	1.45073	0.94	0.0904	18
	Dry	4.06014	1.05285	0.72201	1.41295	0.94	0.0945	18
Hickory	Green	1.73761	1.41142	5.78715	1.16054	0.98	0.0576	54
	Dry	1.17992	1.40117	4.27343	1.13282	0.98	0.0614	54
Black oak	Green	2.14218	1.34513	7.56363	1.08208	0.99	0.0529	27
	Dry	1.27041	1.341323	5.90002	1.02003	0.98	0.0585	27
Chestnut oak	Green	1.38351	1.45567	8.16034	1.08563	0.98	0.0653	51
	Dry	0.89495	1.44204	5.38410	1.06787	0.98	0.0625	51
North. red oak	Green	5.08849	1.19370	6.64281	1.13812	0.99	0.0452	71
	Dry	3.11987	1.17348	3.82608	1.13093	0.99	0.0467	71
Scarlet oak	Green	1.54710	1.42294	6.43469	1.12574	0.99	0.0471	27
	Dry	0.90818	1.41531	4.32971	1.08964	0.99	0.0507	27
White oak	Green	2.54174	1.32196	4.71951	1.19292	0.98	0.0646	28
	Dry	1.59285	1.31179	3.42725	1.152112	0.98	0.0682	28
All Species	Green	3.11290	1.26260	4.03992	1.20824	0.97	0.0790	475
	Dry	1.73051	1.27761	2.58728	1.18874	0.96	0.0895	475

Continued

Table 8. --Regression equations for estimating green and dry weight of the total-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. as the independent variable--Continued

Species or species group	Weight green or dry	Regression equation coefficients				Coefficient of determination (R^2)	Standard error? ($S_{y \cdot x}$)	No. of trees sampled		
		Trees < 11.0 in d.b.h. ¹		Trees > 11.0 in d.b.h. ²						
		a'	b	a''	b	TOTAL-STEM WOOD				
Soft Hardwoods	Green	2.46606	1.26259	2.51860	1.25819	0.97	0.0793	128		
	Dry	1.06273	1.29440	1.10764	1.28577	0.96	0.0894	128		
Basswood	Green	2.30938	1.25892	3.31591	1.18348	0.98	0.0514	18		
	Dry	1.12481	1.23786	0.90690	1.78276	0.98	0.0635	18		
Blackgum (upland)	Green	1.24971	1.37279	3.29438	1.17059	0.97	0.0820	18		
	Dry	0.55552	1.39637	1.18172	1.23898	0.95	0.0981	18		
Red maple	Green	3.54641	1.19449	6.97484	1.05346	0.97	0.0659	30		
	Dry	1.62534	1.23722	3.67497	1.06711	0.97	0.0619	30		
Yellow-poplar	Green	1.80879	1.35110	3.57285	1.20916	0.98	0.0607	62		
	Dry	0.66009	1.41104	1.43045	1.24978	0.99	0.0609	62		
Hard Hardwoods	Green	2.28723	1.30180	3.88139	1.19153	0.97	0.0813	347		
	Dry	1.46631	1.29169	3.05149	1.13887	0.97	0.0778	347		
White ash	Green	3.25897	1.19382	3.63679	1.17098	0.97	0.0686	52		
	Dry	2.37705	1.18055	2.58557	1.16301	0.97	0.0697	52		
Sweet birch	Green	5.03040	1.12103	4.30529	1.15349	0.98	0.0588	21		
	Dry	2.97489	1.11933	7.78946	1.13275	0.98	0.0587	21		
Black locust	Green	4.83873	1.06808	0.10544	1.46959	0.94	0.0955	18		
	Dry	3.41664	1.06056	0.60942	1.42002	0.94	0.0948	18		
Hickory	Green	1.17748	1.46100	4.78689	1.16855	0.98	0.0648	54		
	Dry	0.83461	1.44423	3.67039	1.13540	0.98	0.0684	54		
Black oak	Green	1.41717	1.39770	6.43849	1.1582118	0.98	0.0569	27		
	Dry	0.83649	1.30137	5.50646	0.99842	0.98	0.0642	27		
Chestnut oak	Green	1.02865	1.47458	5.78444	1.11449	0.98	0.0678	51		
	Dry	0.63137	1.46903	3.73598	1.09831	0.98	0.0664	51		
North. red oak	Green	3.49586	1.21777	5.61541	1.14470	0.99	0.0462	71		
	Dry	2.40772	1.19591	3.27347	1.13186	0.99	0.0481	71		
Scarlet oak	Green	1.06906	1.46877	5.10270	1.14286	0.99	u A484	27		
	Dry	0.63385	1.45552	3.45720	1.10180	0.99	0.0526	27		
White oak	Green	2.22827	1.31979	3.83790	1.20642	0.98	0.0660	28		
	Dry	1.38070	1.31206	2.87565	1.15907	0.98	0.0707	28		
All Species	Green	2.32825	1.29147	3.38635	1.21330	0.97	0.0819	475		
	Dry	1.30842	1.29844	2.20176	1.18992	0.95	0.0959	475		

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2)^b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2)^b$$

Where: Y = component weight in pounds

D = tree d.b.h. in inches

a' , a'' , b = regression coefficients

³log₁₀ form

Table 9--Regression equations for estimating cubic-foot volume of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. as the independent variable

Species or species group	Volume wood & bark or wood only	Regression equation		coefficients		Coefficient of determination (R ²)	Standard error ³ (S _{y.x})	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹	Trees > 11.0 in d.b.h. ²	a'	b			
TOTAL TREE								
Soft Hardwoods	W&Bk Wood	0.05802 0.04501	1.28608 1.29710	0.06153 0.05131	1.77383 1.26978	0.98 0.97	0.0663 0.0734	128 128
Basswood	W&Bk Wood	0.07357 0.04976	1.23831 1.27105	0.06447 0.03994	1.26584 1.31689	n.98 0.98	0.0569 0.0554	18 18
Blackgum (upland)	W&Bk Wood	0.04090 0.02912	1.31863 1.33350	0.06364 0.04119	1.22644 1.76120	0.99 0.99	0.0455 0.0510	18 18
Red maple	W&Bk Wood	0.06378 0.04930	1.27295 1.29431	0.15680 0.14248	1.08537 1.07299	0.98 0.98	0.0557 0.0579	30 30
Yellow-poplar	W&Bk Wood	0.04585 0.03886	1.35223 1.34410	0.07195 0.06532	1.24157 1.23584	0.99 0.99	0.0541 0.0555	62 62
Hard Hardwoods	W&Bk Wood	0.05537 0.03915	1.29983 1.32732	0.07301 0.05585	1.24217 1.25324	0.98 0.97	0.0655 0.0753	347 347
White ash	W&Bk Wood	0.08067 0.05529	1.22543 1.26044	0.09913 0.07580	1.18248 1.19466	0.98 0.98	0.0580 0.0600	52 52
Sweet birch	W&Bk Wood	0.11822 0.09520	1.14568 1.15088	0.15666 0.13160	1.08698 1.08336	0.99 0.99	n.0380 0.0446	21 21
Black locust	W&Bk wood	0.10831 0.07412	1.11241 1.17961	0.03519 0.02836	1.34682 1.32995	0.96 0.96	0.0762 0.0783	18 18
Hickory	W&Bk Wood	0.02021 0.01280	1.52367 1.57260	0.06722 0.05106	1.27307 1.28412	0.98 0.98	0.0613 0.0674	54 54
Black oak	Wd&Bk Wood	0.04099 0.02595	1.33969 1.39254	0.05912 0.05279	1.26330 1.24450	0.99 0.99	0.0536 0.0552	27 27
Chestnut oak	Wd&Bk Wood	0.02622 0.01764	1.45566 1.47986	0.09785 0.06883	1.18104 1.19592	0.98 0.98	0.0611 0.0619	51 51
North. red oak	Wd&Bk Wood	0.011970 0.07073	1.20851 1.27312	0.08773 0.07400	1.71314 1.21369	0.99 0.99	0.0442 0.0449	71 71
Scarlet oak	Wd&Bk Wood	0.04951 0.03011	1.31646 1.37901	0.06803 0.04966	1.25020 1.27467	0.99 0.99	0.0453 0.0432	27 27
White oak	Wd&Bk Wood	0.04304 0.03430	1.35273 1.35552	II.04598 0.03445	I.33897 1.35460	0.99 0.99	0.0513 0.0522	28 28
All Species	Wd&Bk Wood	0.05612 0.04091	1.29589 1.31880	0.06974 0.05462	1.25058 1.25751	0.98 0.97	0.0656 0.0745	475 475

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2)b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2)b$$

Where: Y = component volume in cubic feet

D = tree d.b.h. in inches

a', a'', b = regression coefficients

³log₁₀ form

Table I.--Regression equations for estimating cubic-foot volume of the total-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. as the independent variable

Species or species group	Volume wood & bark or wood only	Regression equation coefficients				Coefficient of determination (R^2)	Standard error ³ ($S_{y \cdot x}$)	No. of trees sampled
		Trees < 11.0 in d.b.h.	a'	b	Trees > 11.0 in d.b.h.	a"	b	
TOTAL STEM								
Soft Hardwoods	Wd&Bk Wood	0.05195 0.03947	1.26995 1.29199	0.04238 0.03836	1.317411 1.29797	0.96 0.96	0.0903 0.0933	128 128
Basswood	Wd&Bk Wood	0.06238 0.04157	1.23003 1.27449	0.06487 0.04134	1.22188 1.27562	0.99 0.99	0.0446 0.0460	18 18
Blackgum (upland)	Wd&Bk Wood	0.02124 0.01380	1.40349 1.44717	0.04354 n-03267	1.25385 1.76743	0.98 0.98	0.0628 0.0660	18 18
Red maple	Wd&Bk Wood	0.07559 0.05485	1.17514 1.21982	0.09946 0.10109	1.11791 1.09235	0.97 n.97	11.0663 0.0666	3n 30
Yellow-poplar	Wd&Bk Wood	0.03888 0.03438	1.36861 1.35427	0.08087 0.06773	1.21590 1.21287	0.98 0.98	0.0597 0.0597	62 62
Hard Hardwoods	Wd&Bk Wood	0.05337 0.03738	1.26301 1.29966	0.09024 0.06889	1.15347 1.17215	0.98 0.97	0.0672 0.0741	347 347
White ash	Wd&Bk Wood	0.09402 0.06326	1.14061 1.18725	0.06737 0.05445	1.21012 1.21852	0.97 0.97	0.0750 0.0758	52 52
Sweet birch	Wd&Bk Wood	0.08453 0.07232	1.14744 1.15397	0.12361 0.12089	1.06818 1.04683	0.98 0.98	0.0474 0.0520	21 21
Black locust	Wd&Bk Wood	0.10288 0.06691	1.08093 1.11710	0.02191 0.02106	1.40339 1.35819	0.94 n.94	0.0948 0.0913	18 18
Hickory	Wd&Bk Wood	0.02510 0.01480	1.42907 1.50277	0.08166 0.06279	1.18313 1.20138	0.98 0.98	0.0598 0.0667	54 54
Black oak	Wd&Bk Wood	0.04054 0.02568	1.31045 I. 36870	0.11881 0.09878	1.08626 1.08776	n.99 0.99	0.0509 0.0529	27 27
Chestnut oak	Wd&Bk Wood	0.02746 0.01793	1.47145 1.45245	0.19753 0.09736	1.06004 1.09965	0.98 0.98	0.0602 0.0617	51 51
North. red oak	Wd&Bk Wood	0.09105 0.07170	1.15950 1.17986	0.09673 0.08156	1.14688 1.15300	0.99 0.99	0.0451 0.0456	71 71
Scarlet oak	Wd&Bk Wood	0.02603 0.01730	1.40341 1.45519	0.08946 0.06724	1.14595 1.17208	0.99 0.99	0.0465 0.0465	27 27
White oak	Wd&Bk Wood	0.03821 0.03097	1.33563 1.34368	U. 08641 0.06420	1.16549 1.19163	0.98 0.98	0.0602 0.0607	28 28
All Species	Wd&Bk Wood	0.05279 0.03798	1.26592 1.29756	0.07606 0.06054	1.18976 1.20033	u.97 0.97	0.0760 0.0810	475 475

¹Trees < 11.11 inches d.b.h.

$$Y = a'(D^2)^b$$

²Trees ≥ 11.0 inches d.b.h.

$$Y = a''(D^2)^b$$

Where: Y = component volume in cubic feet

D = tree d.b.h. in inches

a' , a'' , b = regression coefficients

³ \log_{10} form

Table 11.--Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.h.h. and total height as the independent variables

Species or species group	Weight green or dry	Regression equation coefficients						Coefficient of determination (R^2)	Standard error of estimate (S_{y-x})	No. of trees sampled
		Trees < 11.0 in d.h.h. ¹		Trees > 11.0 in d.b.h. ²		a'	b	c		
TOTAL-TREE WOOD AND BARK										
Soft Hardwoods	Green	0.31602	0.91874	0.20742	1.00653	0.91874	0.97	0.0707	128	
	Dry	0.16021	U. 91717	0.08941	1.03878	0.91717	0.96	0.0936	128	
Basswood	Green	0.09136	1.05036	0.14541	0.95344	1.05036	0.98	0.0505	18	
	Dry	0.05335	1.02167	0.04667	1.04954	1.02167	0.98	0.0603	18	
Blackgum (upland)	Green	II. 47487	0.88913	0.36480	0.94411	0.88913	0.98	0.0601	18	
	Dry	0.20398	0.91126	0.14438	0.98332	0.91126	0.98	0.0621	18	
Red maple	Green	0.16008	1.01323	0.34839	0.85107	1.01323	0.98	0.0544	30	
	Dry	0.07954	1.02615	0.16035	0.87996	1.02615	0.98	0.0547	30	
Yellow-poplar	Green	0.19596	U.96111	0.13363	1.04093	0.96111	0.49	0.0550	62	
	Dry	0.05841	1.01185	0.04445	1.06881	1.01185	0.49	0.0506	62	
Hard Hardwoods	Green	0.19669	0.98801	0.11131	1.10671	0.98801	0.98	0.0702	347	
	Dry	0.12092	0.98756	0.08018	1.07324	0.98756	n.98	0.0625	347	
White ash	Green	0.21956	0.96160	0.24471	0.93899	0.96161)	0.97	0.0654	52	
	Dry	0.15213	0.96987	0.19074	0.92271	0.96987	0.97	0.0673	52	
Sweet birch	Green	0.44356	U.90980	0.20032	1.07555	0.90980	0.99	0.0358	21	
	Dry	(I.26925	0.90717	0.12181	1.07256	0.90717	0.99	0.0389	21	
Black locust	Green	0.63183	0.82875	0.14351~	1.13781	0.82875	0.97	0.0658	18	
	Dry	0.41824	0.83091	0.11081	1.10786	0.83091	0.97	0.0703	18	
Hickory	Green	0.06729	1.11301	0.09083	1.05044	1.11301	0.99	0.0493	54	
	Dry	0.04484	1.10947	0.06609	1.02860	1.10947	0.99	0.0497	54	
Black oak	Green	0.15621	1.00554	0.06290	1.19522	1.00554	0.99	0.0436	27	
	Dry	0.09126	1.00484	0.04390	1.15741	1.00484	0.99	0.0500	27	
Chestnut oak	Green	0.12392	1.03751	0.09386	1.09544	1.03751	0.98	0.0598	51	
	Dry	0.08257	1.02692	0.06110	1.08969	1.07697	0.99	0.0591	51	
North. red oak	Green	0.33662	0.97831	0.17965	1.03575	0.97831	0.99	0.0395	71	
	Dry	0.14824	0.96680	0.10553	1.03766	0.96680	0.99	0.0439	71	
Scarlet oak	Green	0.26569	0.97104	0.21019	1.01990	0.97104	0.99	0.0396	27	
	Dry	0.15176	0.97144	0.13286	0.99918	0.97144	0.99	0.0419	27	
White oak	Green	0.24482	0.96607	0.08487	1.18696	0.96607	0.99	0.0420	28	
	Dry	0.14990	n.96325	0.05823	1.16040	0.96325	0.99	0.0437	28	
All Species	Green	0.25451	0.95414	0.12346	1.10498	0.95414	0.97	0.0797	475	
	Dry	0.15774	0.94683	0.07345	1.10620	0.94683	0.95	0.1017	475	

Continued

Table 11. -- Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and total height as the independent variables--Continued

Species or species group	Weight green or dry	Regression equation coefficients						Coefficient of determination (R^2)	Standard error ³ ($S_{y \cdot x}$)	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹		Trees > 11.0 in d.b.h. ²		h	c			
TOTAL-TREE WOOD										
Soft Hardwoods	Green	0.23311	0.93122	0.15977	1.00999	0.93122	0.97	0.0763	128	
	Dry	0.11091	0.93642	0.06709	1.04123	n.93642	0.96	0.0974	128	
Basswood	Green	0.06023	1.06970	0.08407	1.00015	1.06970	0.98	0.0527	18	
	Dry	0.03219	1.04781	0.02456	1.10418	1.04781	0.97	0.0669	18	
Blackgum (upland)	Green	0.33390	0.90895	II. 30966	0.92466	n. 90895	(1.98	0.0647	18	
	Dry	0.13582	0.93072	0.10799	0.97855	0.93072	0.98	0.0773	18	
Red maple	Green	0.11327	1.03393	0.30305	0.82873	1.03393	0.98	0.0529	30	
	Dry	0.05210	1.05514	0.13766	n. 85253	1.05514	0.98	0.0546	30	
Yellow-poplar	Green	n. 13651	0.97924	0.10017	1.04379	n. 97924	0.99	0.0553	62	
	Dry	0.04912	1.01161	0.03699	1.07073	1.01161	0.99	0.0508	62	
Hard Hardwoods	Green	0.13063	1.01304	0.08669	1.09853	1.01304	0.98	0.0710	347	
	Dry	0.08244	1.01028	0.06680	1.05416	1.01028	0.98	0.0636	347	
White ash	Green	0.12941	1.00033	0.18612	0.92456	1.00033	0.98	0.0636	52	
	Dry	0.09735	0.99043	0.13839	0.91706	0.99043	0.97	0.0671	52	
Sweet birch	Green	0.32861	0.92113	0.15693	1.07523	0.92113	0.99	0.0358	21	
	Dry	0.21465	0.90970	0.10348	1.06186	0.90970	0.99	0.0400	21	
Black locust	Green	0.364130 5142	0.88256,82824	0.10250	1.16894	0.83256	0.96	0.0722	18	
	Dry			0.08353	1.13573	0.82824	0.96	0.0727	18	
Hickory	Green	0.04243	1.14287	0.07024	1.03779	1.14287	0.99	0.0506	54	
	Dry	0.02982	1.13570	0.05406	1.01167	1.13570	0.99	0.0530	54	
Black oak	Green	0.09092	1.04481	0.05014	1.16891	1.04481	0.99	0.0447	27	
	Dry	0.99231	1.04328	0.99230	1.16891	1.04328	0.99	0.0530	27	
Chestnut oak	Green	0.09113	1.04647	0.06928	1.10364	1.04647	0.99	0.0585	51	
	Dry	0.05684	1.04198	0.04387	1.09602	1.04198	0.99	0.0594	51	
North. red oak	Green	0.1731%	0.99498	0.14480	1.03223	0.99498	0.99	0.0397	71	
	Dry	0.10808	0.98245	0.08739	1.02675	0.98245	0.99	0.0443	71	
Scarlet oak	Green	0.15089	1.01381	0.14609	1.02054	1.01381	0.99	0.0361	27	
	Dry	0.09311	1.00441	0.09709	0.99569	1.00441	0.99	0.0404	27	
White oak	Green	0.20358	0.96705	0.07117	1.15619	0.96705	0.99	0.0377	28	
	Dry	0.12347	0.96604	0.115037	1.15300	0.96604	0.99	0.0411	28	
All Species	Green	0.17494	0.97508	0.09590	1.10044	0.97508	0.97	0.0821	475	
	Dry	0.10805	0.96858	0.05945	1.09315	0.96858	0.95	0.1042	475	

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2 Th)^b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2)^b (Th)^c$$

Where : Y = component weight in pounds

D = tree d.b.h. in inches

Th = tree total height in feet

a' , a'' , b , c = regression coefficients

³log₁₀ form

Table 12.--Regression equations for estimating green and dry weight of the total-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and total height as the independent variables

Species or species group	Weight green or dry	Regression equation coefficients						Coefficient of determination (R^2)	Standard error ³ ($S_{y,x}$)	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹		Trees > 11.0 in d.b.h. ²		a ¹	b	a ²	b	
TOTAL-STEM WOOD AND BARK										
Soft Hard woods	Green	0.19934	Cl. 94973	0.16133	0.99384	0.94973	0.99	0.0518	128	
	Dry	0.09888	0.95125	0.06854	I. 02768	tr.95125	0.98	0.0705	128	
Basswood	Green	0.08821	1.03198	0.16014	0.90765	1.03198	0.99	0.0442	18	
	Dry	0.05129	1. 00461	0.04977	1.01089	1.00461	0.98	0.0554	18	
Blackgum (upland)	Green	U. 15859	0.98515	0.22795	0.90950	11.08515	0.99	0.0402	18	
	Dry	0.06880	1. 00676	0.08988	0.95103	1.00676	0.99	0.0439	18	
Red maple	Green	0.22441	0.94430	0.31468	0.87381	0.04430	0.98	0.0496	30	
	Dry	0.10581	0.96411	0.14771	0.89455	0.96411	0.98	0.0479	30	
Yellow-poplar	Green	0.15121	0.97890	0.13749	0.49873	0.97890	n.99	0.0478	62	
	Dry	0.04546	1.03017	0.04582	1.02854	1.03017	n.99	0.0451	62	
Hard Hardwoods	Green	0.17993	0.97590	0.15338	1. 00919	0.97590	0.98	0.0595	347	
	Dry	0.11152	U.97453	0.11745	0.96373	0.97453	0.98	0.0517	347	
White ash	Green	0.23622	0.92708	0.72621	0.93611	0.92708	0.98	0.0522	52	
	Dry	0.15030	0.93298	0.15789	0.92271	0.93298	0.98	0.0557	52	
Sweet birch	Green	0.31103	0.91450	0.16546	1.04610	0.91450	0.99	0.0285	21	
	Dry	0.18284	0.91559	0.10396	1.03331	0.91559	0.99	0.0301	21	
Black locust	Green	0.57284	0.81908	0.10412	1.17462	0.81908	0.96	0.0735	18	
	Dry	0.39304	0.81739	0.08647	1.13311	0.81739	0.96	0.0767	18	
Hickory	Green	0.09583	1.05114	0.14380	0.96651	1.05114	0.99	0.0405	54	
	Dry	0.06362	1.04848	0.10916	0.93591	1.04848	0.99	0.0408	54	
Black oak	Green	0.14548	0.99793	0.13822	1.00861	0.09793	0.99	0.0314	27	
	Dry	0.08687	0.99464	0.10937	0.94660	0.99464	0.99	0.0399	27	
Chestnut oak	Green	0.12840	1.01954	0.15468	0.98071	1.01954	0.99	0.0513	51	
	Dry	0.08603	1.00853	0.10592	0.96515	1.00853	0.99	0.0495	51	
North. red oak	Green	0.24070	0.95415	0.23072	0.96299	0.95415	0.99	0.0310	71	
	Dry	0.15595	0.93760	0.14071	0.95903	0.93760	0.99	0.0340	71	
Scarlet oak	Green	0.11172	1.04344	0.24082	0.88329	1.04344	0.99	0.0217	27	
	Dry	0.06479	1.04088	0.16509	0.84587	1.04088	0.99	0.0238	27	
White oak	Green	0.20662	0.96388	0.16762	1.00750	0.96388	0.99	U.0406	28	
	Dry	0.12930	0.95884	0.12498	0.96593	0.95884	0.99	0.0439	28	
All Species	Green	0.19770	0.96086	0.14855	1.02045	0.96086	0.98	0.0630	475	
	Dry	0.12095	0.95501	0.09243	1.01108	0.95501	U.96	0.0826	475	

Continued

Table 12.--Regression equations for estimating green and dry weight of the total-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and total height as the independent variables--Continued

Species or species group	Weight green or dry	Regression equation coefficients						Coefficient of determination (R ²)	Standard error ³ (S _{y,x})	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹		Trees > 11.0 in d.b.h. ²		a'	b	a"	b	c
TOTAL-STEM WOOD										
Soft Hardwoods	Green	0.15261	0.96172	0.13246	0.99124	0.96172	0.98		0.0573	128
	Dry	0.06892	0.97261	0.05358	1.02508	0.97261	0.97		0.0786	128
Basswood	Green	0.05550	1.06156	0.09094	0.95858	1.06156	0.99		0.0490	18
	Dry	0.02942	1.04125	0.02627	1.04125		0.98		0.0635	18
Blackgum (upland)	Green	0.10942	1.01097	0.20976	0.87527	1.01097	0.99		0.0474	18
	Dry	0.04376	1.03588	0.07373	13.92852	1.03588	0.98		0.0639	18
Red maple	Green	0.14686	0.97841	0.27906	0.84461	0.97847	0.98		0.0491	30
	Dry	0.06349	1.00702	0.12853	0.85996	1.00702	0.98		0.0494	30
Yellow-poplar	Green	0.12422	0.98142	0.10984	1.00707	0.98142	0.99		0.0489	62
	Dry	0.03932	1.02757	0.03764	1.03668	1.02757	U.99		0.0453	62
Hard Hardwoods	Green	0.12083	1.00298	0.11700	1.00970	1.00298	0.98		0.0613	347
	Dry	0.07607	0.99989	0.09454	0.95455	0.99989	0.98		0.0535	347
White ash	Green	0.14063	0.96902	0.17946	0.91817	0.96902	0.98		0.0532	52
	Dry	0.10748	0.95689	0.13168	0.91455	0.95689	0.98		0.0559	52
Sweet birch	Green	0.25981	0.91883	0.14974	1.03374	0.91883	0.99		0.0340	21
	Dry	0.15736	0.91519	0.09736	1.01531	0.91519	0.99		0.0363	21
Black locust	Green	0.44948	0.83007	0.08217	1.18441	0.83007	0.96		0.0768	18
	Dry	0.32742	0.82255	0.07165	1.13438	0.82255	0.96		0.0772	18
Hickory	Green	0.05624	1.09284	0.10452	0.96359	1.09284	0.99		0.0442	54
	Dry	0.03952	1.08526	0.08380	0.92852	1.08525	0.99		0.11450	54
Black oak	Green	0.08573	1.03812	0.10050	1.00496	1.03812	0.99		0.0344	27
	Dry	0.06028	1.03559	0.08744	0.92022	1.03559	0.99		0.0439	27
Chestnut oak	Green	0.09235	1.03304	0.10413	1.00801	1.03304	0.99		II.0538	51
	Dry	0.06798	1.02760	0.116828	0.99350	1.02760	0.99		0.0536	51
North. red oak	Green	0.17657	0.97299	0.18231	0.96632	0.97299	0.99		0.0321	71
	Dry	0.11374	0.95543	11.11302	0.95675	0.95543	0.99		0.0354	71
Scarlet oak	Green	0.07051	1.07773	0.17181	0.89202	1.07773	0.99		0.0205	27
	Dry	0.04141	1.07196	0.17017	0.84980	1.07195	U.99		0.0223	27
White oak	Green	0.17712	0.96533	0.13718	1.01862	0.96533	0.99		0.0393	28
	Dry	0.10869	0.96249	0.10490	0.96989	0.96249	0.99		11.0441	28
All Species	Green	II.13914	0.98254	0.11546	1.02144	0.98254	0.98		0.0660	475
	Dry	n.08352	0.97859	0.07357	1.00504	0.97859	0.96		0.0873	475

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2 Th)^b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2)^b (Th)^c$$

Where: **Y** = component weight in pounds

D = tree d.b.h. in inches

Th = tree total height in feet

a', a'', b, c = regression coefficients

³log₁₀ form

Table 13.--Regression equations for estimating cubic-foot volume of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and total height as the independent variables

Species or species group	Volume wood & bark or wood only	Regression equation coefficients						Coefficient of determination (R^2)	Standard error ³ ($S_{y,x}$)	No. of trees sampled
		'Trees < 11.0 in d.b.h.'		'Trees > 11.0 in d.b.h.'		a''	b	c		
TOTAL TREE										
Soft Hardwoods	Wd&Bk Wood	0.00377 0.00269	0.06802 0.98343	0.00304 0.00248	1.01320 0.99998	0.96802 0.98343	0.99 0.99	0.0494 0.0518	178 128	
Basswood	Wd&Bk Wood	0.00182 0.00113	1.04757 1.07381	0.00189 0.00106	1.04029 1.08723	1.04757 1.07381	0.98 0.98	0.0520 0.0513	18 18	
<i>Black gum (upland)</i>	Wd&Bk Wood	0.00558 0.00364	0.93016 0.94820	0.00404 0.00259	0.09741 1.01950	0.93016 0.94820	0.99 0.99	0.0507 0.0476	18 18	
<i>Red maple</i>	Wd&Bk Wood	0.00240 0.00171	1.02973 1.05004	0.00488 0.00423	0.88130 0.86117	1.02973 1.05004	0.98 0.99	0.0482 0.0471	30 30	
<i>Yellow-poplar</i>	Wd&Bk Wood	0.00311 0.00267	0.98332 0.97804	0.00239 0.00204	1.03846 1.03346	0.98332 0.97804	0.99 0.99	0.0391 0.0405	62 62	
Hard Hardwoods	Wd&Bk Wood	0.00351 0.00216	0.98106 1.01097	0.06221 0.00157	1.07756 1.07753	0.98106 1.01097	0.98 n.98	0.0556 0.0606	347 347	
<i>White ash</i>	Wd&Bk wood	0.00389 0.00240	0.97227 1.00222	0.00437 0.00306	0.94831 0.95133	0.97777 1.00227	0.98 0.98	0.0578 0.0581	52 52	
<i>Sweet birch</i>	Wd&Bk Wood	0.00754 0.00547	0.90703 0.92188	u.00495 0.00412	0.99501 U.98078	u.90703 0.92188	u.99 0.99	0.0378 u.0344	21 21	
<i>Black locust</i>	Wd&Bk Wood	0.01034 0.00665	U.84979 U.86588	0.00356 0.00280	1.07222 1.04662	0.84979 U.86588	0.97 0.97	0.0606 u.0604	18 18	
<i>Hickory</i>	Wd&Bk Wood	0.00102 0.00056	1.11877 1.16061	0.00124 u.00083	1.07735 1.07704	1.11817 1.16061	0.99 IJ.99	0.0579 U.0593	54 54	
<i>Black oak</i>	Wd&Bk Wood	0.00318 0.00179	0.97999 1.02067	0.00111 0.00085	1.19925 1.17661	0.97999 1.02067	0.99 0.99	0.0455 0.0451	27 27	
<i>Chestnut oak</i>	Wd&Bk Wood	0.00266 0.00168	1.00944 1.02897	0.00185 0.00122	1.08446 1.09546	1.00944 1.02897	0.99 0.99	0.0562 0.0542	51 51	
North. <i>red oak</i>	Wd&Bk Wood	0.00448 0.00336	0.95561 0.96872	U.00294 0.00238	1.04314 1.04053	0.95561 0.96372	0.99 U.99	0.0384 0.0379	71 71	
<i>Scarlet oak</i>	Wd&Bk Wood	0.00494 0.00264	0.95073 0.99805	0.00324 0.00205	1.03857 1.05112	0.95073 0.99805	0.99 0.99	0.0418 0.0368	27 21	
<i>White oak</i>	Wd&Bk Wood	0.00371 0.00284	0.97305 0.97894	0.00150 0.00112	1.16096 1.17278	0.97305 0.97894	0.99 0.99	0.0366 0.0321	28 28	
All Species	Wd&Bk Wood	0.00375 0.00242	0.97203 0.99723	0.00234 0.00174	1.07007 1.06639	0.97203 0.99723	0.98 0.98	0.0557 0.0599	475 475	

¹Trees < 11.0 inches d.b.h.

$$V = a'(D^2)h^b$$

²Trees > 11.0 inches d.b.h.

$$V = a''(D^2)h^b$$

Where: V = component volume in cubic feet

D = tree d.b.h. in inches

Th = tree total height in feet

a' , a'' , b , c = regression coefficients

³log₁₀ form

Table 14.--Regression equations for estimating cubic-foot volume of the total-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and total height as the independent variables

Species or species group	Volume wood & bark or wood only	Regression equation coefficients						Coefficient of determination (R^2)	Standard error ³ ($S_{y,x}$)	No. of trees sampled
		Trees < 11.0 inches d.b.h. ¹		Trees > 11.0 inches d.b.h. ²						
		a'	b	a''	b	c				
TOTAL STEM										
Soft Hardwoods	Wd&Bk Wood	0.00232 0.00166	1.00250 1.02072	0.00224 0.00193	1.00966 0.98916	1.00250 1.02072	0.99 0.99	0.0403 0.0432	128 128	
Basswood	Wd&Bk Wood	0.00160 0.00094	1.03943 1.07630	0.00194 0.00109	0.99928 1.04587	1.03943 1.07630	0.99 0.99	0.0395 0.0415	18 18	
Blackgum (upland)	Wd&Bk Wood	0.00201 0.00116	1.01801 1.05448	0.00250 0.00174	0.97272 0.47115	1.01801 1.05448	0.99 0.99	0.0342 0.0283	18 18	
Red maple	Wd&Bk Wood	0.00313 0.00205	0.96860 1.00321	0.00427 0.00382	0.90395 0.87340	0.96860 1.00321	0.99 0.99	0.0437 0.0446	30 30	
Yellow-poplar	Wd&Bk Wood	U 0.00235 0.00215	1.00446 0.99360	0.00237 0.00206	1.00309 1.00256	1.00446 0.99360	0.99 0.99	cl.0359 0.0369	62 62	
Hard Hardwoods	Wd&Bk Wood	0.00320 0.00196	0.96878 1.00246	11.00302 0.00209	0.98064 0.98968	0.96878 1.00246	0.99 0.99	0.0465 0.0505	347 347	
White ash	Wd&Bk Wood	0.00432 0.00262	0.93473 0.97061	0.00386 0.00276	0.95852 0.95927	0.93473 0.97061	0.98 0.98	0.0563 0.0574	52 52	
Sweet birch	Wd&Bk Wood	0.00446 0.00362	(1.93001 0.93932	0.00394 0.00379	0.95556 0.92974	0.93001 0.931932	0.99 0.99	0.0250 0.0276	21 21	
Black locust	Wd&Bk wood	0.00935 0.00559	0.83921 0.86772	0.00248 0.00222	1.11605 1.06058	0.83921 0.86772	0.96 0.97	0.0760 0.0697	18 18	
Hickory	Wd&Bk wood	0.00144 0.00071	1.05555 1.11439	0.00193 0.00123	0.99419 0.99890	1.05555 1.11439	0.99 0.99	0.0515 0.0548	54 54	
Black oak	Wd&Bk Wood	0.00311 0.00174	0.96620 1.01004	0.00242 0.00169	1.01863 1.01653	0.96620 1.01004	0.99 0.99	0.0360 0.0362	27 27	
Chestnut oak	Wd&Bk Wood	0.00282 0.00173	0.98847 1.01362	0.00321 0.00186	0.96142 0.99799	0.98847 1.01362	0.99 0.99	0.0501 0.0507	51 51	
North. red oak	Wd&Bk Wood	0.00463 0.00348	0.97849 0.94423	0.00370 0.00294	0.97558 0.97909	0.92849 0.94423	0.99 0.99	0.0302 0.0308	71 71	
Scarlet oak	Wd&Bk Wood	0.00197 0.001 lo	1.02777 1.06556	0.00350 0.00233	0.90801 0.92547	1.02777 1.06556	0.99 0.99	(I.0241 0.0218	27 27	
White oak	Wd&Bk Wood	0.00307 0.00242	0.97217 0.97936	0.00296 0.00216	0.97964 1.00348	0.97217 0.97936	0.99 0.99	0.0349 0.0335	28 28	
All Species	Wd&Bk Wood	0.00286 0.00186	0.98063 1.00839	0.00278 0.00204	0.98659 0.98927	0.98063 1.00839	0.99 0.99	0.0453 U.0486	475 475	

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2 Th)^b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2) b(Th)^c$$

Where : Y = component volume in cubic feet

D = tree d.b.h. in inches

Th = tree total height in feet

a', a'', b, c = regression coefficients

³log₁₀ form

Table 15. --Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and height to a 4-inch top as the independent variables

Species or species group	Weight green or dry	Regression equation coefficients						Coefficient of determination (R^2)	Standard errors ($S_{y,x}$)	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹		Trees > 11.0 in d.b.h. ²		a''	b	c		
TOTAL-TREE YOOD AND BARK										
Soft Hardwoods	Green	3. 87800	0. 66860	0.72890	1.01714	0.66860	0.98	0.0666	128	
	Dry	1. 95868	0. 66739	0. 31347	1.04946	U. 66739	0.96	0.0907	128	
Hasswood	Green	2. 04305	0. 73478	0. 58172	0.99672	0.73478	0.98	0.0540	18	
	Dry	1.06650	0.71797	0. 18270	1. 08586	0. 71797	0.98	0.0597	18	
Blackgum (upland)	Green	4. 23896	0. 67201	1.37469	0.90682	0.67201	0.48	0.0638	18	
	Dry	1.94174	0.68751	0.55848	0. 94735	0.68751	0.98	0.0673	18	
Red maple	Green	2.79645	0. 72718	1. 33332	0.88163	0. 72718	0.98	0.0540	3u	
	Dry	1. 48526	0. 73274	0.61053	0.91811	0.73274	0.98	0.0593	30	
Yellow-poplar	Green	3. 11197	0.68358	0.49999	1.06483	n.68358	u.99	0.0506	62	
	Dry	1.08338	0. 71857	0. 17801	1.09515	0.71857	0.99	0. 0468	62	
Hard Hardwoods	Green	2. 39226	0. 73786	0. 37669	1.12332	0.73786	n.97	0.077)	347	
	Dry	1. 43617	0. 74025	0. 27244	1.08687	0.74025	0.98	0.0690	347	
White ash	Green	2.50718	0. 71370	0.57204	1.02182	0.717711	0.96	u.0809	52	
	Dry	1. 58972	0. 71973	0.40270	1.00605	0. 71973	0.96	0. 0825	52	
Sweet birch	Green	4. 04501	n.69652	0. 78224	1.03912	0.69652	0.99	0.0337	21	
	Dry	2. 40566	0. 69623	0. 47615	1.03399	0.69623	II.99	0. 0347	21	
Black locust	Green	1. 94396	0. 73625	0.52809	1.00799	0.73625	0.98	0.0557	18	
	Dry	1. 31417	0. 73594	0. 40396	0.98192	0.73594	0.97	0.0627	18	
Hickory	Green	1. 63821	0. 78657	0. 37653	1.09317	0.78657	0.98	u.0646	54	
	Dry	1. 06957	0. 78530	0. 27338	1.06975	0.78530	0.98	0.0635	54	
Black oak	Green	1. 53755	0. 78627	0. 29164	1.13291	U.78627	n.99	0.0415	27	
	Dry	0. 86880	0. 78956	0. 20407	1.09162	0.78956	0.99	0. 0443	27	
Chestnut oak	Green	1. 36133	0. 79879	0. 33655	1.09018	0.79879	0.98	0.0608	51	
	Dry	0. 88762	0. 79030	0. 21614	1.08485	0.79030	0.98	0.0604	51	
North. red oak	Green	2. 01988	II. 77154	0.61891	1.01818	0.77154	0.99	0.0438	71	
	Dry	1. 23446	0. 76241	0. 35828	1.02036	0.76241	0.99	0. 0478	71	
Scarlet oak	Green	4.10752	0.69123	0. 70194	1.05962	0.69123	0.99	0.0431	27	
	Dry	2. 35170	0. 69136	0. 44376	1.03909	0.69136	0.99	0.0454	21	
White oak	Green	3. 58815	0. 69390	0. 27149	1.23218	0.69390	0.99	0.0502	28	
	Dry	2. 18335	0. 69168	II. 18557	1.20572	0.69168	0.99	0.0519	28	
All Species	Green	2. 95488	0. 70930	0. 42263	1.11480	0.70930	0.97	0.0818	475	
	Dry	1. 69369	0.71102	0. 25268	1.10773	0.71102	0. 95	0.0995	475	

Continued

Table 15.--Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and height to a 4-inch top as the independent variables--Continued

Species or species group	Weight green or dry	Regression equation coefficients						Coefficient of determination (R^2)	Standard error ³ (S_{y-x})	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹		Trees > 11.0 in d.b.h. ²		A ^b	B ^b	C ^b		
TOTAL-TREE WOOD										
Soft Hardwoods	Green	2. 96375	0. 67752	0.57084	1.02096	0.67752	0.97	0.0726	128	
	Dry	1. 45160	0. 67951	0.2402"	1.05463	0.67951	0.96	0.0957	128	
Basswood	Green	1. 39838	0. 75067	0.34907	1.041305	0. 75067	0.98	0.0533	18	
	Dry	0. 67563	0. 7397"	0.10124	1.13550	0.73970	0.98	0.0629	18	
Blackgum (upland)	Green	3. 23948	0. 68264	1.17299	0.89447	0.68264	0.97	0.0727	18	
	Dry	1.41496	0.6969"	0.41741	0.95146	0.69690	0.96	0.0862	18	
Red maple	Green	2.09711	0. 74209	1.19238	n. 85982	0. 74209	n. 98	0.0524	30	
	Dry	1.04762	0.75450	0.54780	0.88970	0.75450	0.98	0.0580	30	
Yellow-poplar	Green	2.27879	0. 69674	0.38437	1. "6786	0.69674	0.99	0.0504	62	
	Dry	0.91051	0.71839	0.14811	1.09707	0.71839	0.99	0.0470	62	
Hard Hardwoods	Green	1.70092	0.75597	n. 30231)	1. 11618	0. 75597	0.97	0.0794	347	
	Dry	1.04156	0.75671	0.23324	1. 06873	0. 75671	0.97	0.0707	347	
White ash	Green	1.61925	0.74327	0.45156	1. 00955	0. 74327	0.96	0.0800	52	
	Dry	1.195113	0.73519	0.33202	1. 00224	0. 73519	0.96	0.0831	52	
Sweet birch	Green	3.14751	0. 70253	0.61852	1. 04179	0. 70253	0.99	0.0374	21	
	Dry	1.96765	0.69518	0.40326	1. 02628	0. 69578	0.99	0.0390	21	
Black locust	Green	1.60581	0.73849	0.37694	1. 04069	0. 73849	0.97	U.0639	18	
	Dry	1.13645	0.73395	0.30391	1. 00897	0. 73395	0.97	U.0651	18	
Hickory	Green	1.12061	0.80821	0.30283	1.08104	0. 80821	0.98	0.0657	54	
	Dry	0. 77109	0.80320	0.23097	1. 05457	0.80320	0.98	0.0674	54	
Black oak	Green	0.99751	0.81466	0.24632	1. 10630	0. 81466	0.99	0.0451	27	
	Dry	0.56446	U.81742	0.19472	1. 03934	0. 81742	0.99	0.0496	27	
Chestnut oak	Green	1.01223	0.80684	0.25162	1. 09709	0. 80684	0.99	0.0582	51	
	Dry	0.62573	0.80321	0.15840	1.08967	0. 80321	n. 99	0.0593	51	
North. red oak	Green	1.53212	0.78474	0.50950	1. 01431	0. 78474	0.99	0.0441	71	
	Dry	0.93166	0.77473	0.30265	1.00918	0. 77473	0.99	0.0483	71	
Scarlet oak	Green	2.65815	0.72045	U.51314	1. 06342	0. 72045	0.99	U.0420	27	
	Dry	1.60282	0.71334	0.33673	1.03867	U. 71334	0.99	U.0462	27	
White oak	Green	3.02013	0. 69348	0.2274"	1. 23277	0.69348	0.99	0.0483	28	
	Dry	1.83047	U.69249	U.16065	1.19983	0.69249	0.99	0.0514	28	
All Species	Green	2.15321	0.72432	0.3369U	1.11110	0.72432	0.97	0.0845	475	
	Dry	1.23430	(1.72643	0.21000	1.09577	0.72643	0.95	0.1024	475	

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2H4)^b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2)^b (H4)^c$$

Where: Y = component weight in pounds

U = tree d.b.h. in inches

H4 = tree height to 4-inch top in feet

a', a'', b, c = regression coefficients

Jlog₁₀ form

Table 16.--Regression equations for estimating green and dry weight of the total-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and height to a 1-inch top as the independent variables

Species or species group	Weight green or dry	Regression equation coefficients						Coefficient of determination (R^2)	Standard error ³ (S_{y-x})	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹		Trees > 11.0 in d.b.h. ²						
		a'	b	a''	b	c				
TOTAL-STEM WOOD AND BARK										
Soft Hardwoods	Green	2.70598	0.68917	0.58816	1.00742	0.68917	0.99	0.0485		128
	Dry	1.34721	0.69034	0.25043	1.04120	0.69034	0.98	0.0681		128
Basswood	Green	1.80352	0.72616	0.63852	0.94268	0.72616	0.99	0.0420		18
	Dry	0.94076	0.71033	0.19456	1.03894	0.71033	0.98	0.0496		18
Blackyum (upland)	Green	1.78861	0.74493	0.99337	0.86756	0.74493	0.99	0.0463		18
	Dry	0.83050	0.75941	0.40037	0.91156	0.75941	0.99	0.0526		18
Red maple	Green	3.08548	0.68327	1.13653	0.89152	0.68327	0.99	0.0406		30
	Dry	1.56821	0.69512	0.53992	0.91745	0.69512	0.99	0.0425		30
Yellow-poplar	Green	2.54447	0.69544	0.52654	1.02392	0.69544	0.99	0.0435		62
	Dry	0.89497	0.73079	0.18796	1.05619	0.73079	0.99	0.0418		62
Hard Hardwoods	Green	2.04725	0.73315	0.51514	1.02087	0.73315	0.98	0.0649		347
	Dry	1.23429	0.73505	0.39578	0.97221	0.73505	0.98	0.0552		347
White ash	Green	2.28808	0.69737	0.52864	1.00288	0.69737	0.98	0.0620		52
	Dry	1.47697	0.70182	0.37101	0.98989	0.70182	0.97	0.0651		52
Sweet birch	Green	3.03771	0.69307	0.63758	1.01860	0.69307	0.99	0.0367		21
	Dry	1.76762	0.69548	0.40309	1.00372	0.69548	0.99	0.0360		21
Black locust	Green	1.67174	0.73255	0.38808	1.03707	0.73255	0.97	0.0608		18
	Dry	1.16427	0.72894	0.31758	1.09982	0.72894	0.97	0.0663		18
Hickory	Green	1.88020	0.74741	0.55575	1.00155	0.74741	0.99	0.0513		54
	Dry	1.22829	0.74655	0.42129	0.96967	0.74655	0.99	0.0502		54
Black oak	Green	1.37979	0.78271	0.63488	0.94457	0.78271	0.99	0.0024		27
	Dry	0.78855	0.78452	0.50189	0.87873	0.78452	0.99	0.0281		27
Chestnut oak	Green	1.35011	0.78522	0.54270	0.97525	0.78522	0.99	0.0521		51
	Dry	0.88479	0.77634	0.36639	0.96018	0.77634	0.99	0.0508		51
North. red oak	Green	1.90954	0.75492	0.77247	0.94363	0.75492	0.99	0.0334		71
	Dry	1.19086	0.74208	0.46145	0.93977	0.74208	0.99	0.0359		71
Scarlet oak	Green	2.17715	0.74227	0.87900	0.92654	0.74777	1.00	0.0294		27
	Dry	1.22755	0.74017	0.60029	0.88933	0.74017	1.00	0.0315		27
White oak	Green	2.97960	0.69355	0.53612	1.05120	0.69355	0.99	0.0473		28
	Dry	1.84123	0.68976	0.39718	1.00958	0.68976	0.99	0.0504		28
All Species	Green	2.29643	0.71631	0.51504	1.02802	0.71631	0.98	0.0639		475
	Dry	1.30544	n. 71901	0.32256	1.01051	0.71901	0.97	0.0784		475

Continued

Table 16.--Regression equations for estimating green and dry weight of the total-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and height to a 4-inch top as the independent variables--Continued

Species or species group	Weight green or dry	Regression equation coefficients						Coefficient of determination (R^2)	Standard error ³ ($S_{y,x}$)	No. of trees sampled
		Trees < 11.0 in d.b.h. ¹		Trees > 11.0 in d.b.h. ²		c				
		a'	b	a''	b	c				
TOTAL-STEM WOOD										
Soft Hardwoods	Green	2.1479%	0.69749	0.49031	1.00551	0.69749	0.99	0.0548	128	
	Dry	1.00818	0.70434	0.20072	1.04089	0.70434	0.97	0.0776	128	
Basswood	Green	1.22165	0.74849	0.38011	0.99193	0.74849	0.99	0.0447	18	
	Dry	0.58750	0.73878	0.10930	1.08944	0.73878	0.98	0.0552	18	
Blackgum (upland)	Green	1.36219	0.76003	0.92697	0.84029	0.76003	0.98	0.0591	18	
	Dry	0.59238	0.77606	0.33071	0.89760	0.77606	0.98	0.0763	18	
Red maple	Green	2.22053	0.70795	1.05548	0.86304	0.70795	0.99	0.0393	30	
	Dry	1.05063	0.72725	0.50125	0.88156	0.72725	0.99	0.0415	30	
Yellow-poplar	Green	2.10187	0.69743	0.42224	1.03211	0.69743	0.99	0.0444	62	
	Dry	0.76818	0.72896	0.15386	1.06425	0.72896	0.99	0.0420	62	
Hard Hardwoods	Green	1.48446	n. 75239	0.40565	1.02290	0.75239	0.98	0.0677	347	
	Dry	0.90326	0.75324	0.32831	0.96427	n. 75324	0.98	0.0579	347	
White ash	Green	1.52076	0.72808	0.43468	0.98915	0.72808	0.97	0.0644	52	
	Dry	1.12946	n. 71879	0.31524	0.98489	0.71879	0.97	0.0666	52	
Sweet birch	Green	2.56733	0.69624	0.58049	1.00625	0.69624	0.99	0.0414	21	
	Dry	1.51926	0.69522	0.37731	0.98567	0.69522	0.99	0.0412	21	
Black locust	Green	1.34884	0.74071	0.30875	1.04816	0.74071	0.97	0.0658	18	
	Dry	0.97729	0.73344	U.26517	1.00544	0.73344	0.97	0.0668	18	
Hickory	Green	1.24699	0.77656	U.42581	1.00061	0.77656	0.99	0.0556	54	
	Dry	0.85661	0.77131	0.33818	0.96511	0.77131	0.99	0.0559	54	
Black oak	Green	0.90801	0.81183	0.48979	0.94055	0.81183	0.99	0.0314	27	
	Dry	0.51024	U.81433	0.42621	0.85185	0.81433	0.99	0.0360	27	
Chestnut oak	Green	0.99043	0.79698	0.37229	1.00101	0.79698	0.99	0.5276	51	
	Dry	U.61484	0.79264	0.24243	0.98669	0.79264	0.99	0.0528	51	
North. red oak	Green	1.45796	0.76993	0.62520	U.94648	0.76993	0.99	0.0345	71	
	Dry	0.90260	0.75622	0.37912	0.93710	0.75622	0.99	0.0372	71	
Scarlet oak	Green	1.49501	0.76534	0.652459	0.93822	0.76534	1.00	0.0317	27	
	Dry	0.86961	0.76041	0.45232	0.89671	11.76041	0.99	0.0348	27	
White oak	Green	2.58959	0.69342	0.43846	1.06374	0.69342	0.99	0.0479	28	
	Dry	1.58227	0.69095	0.33384	1.01539	0.69095	0.99	U.0624	28	
All Species	Green	1.72268	0.73146	0.41085	1.03035	U.73146	0.98	0.0678	475	
	Dry	0.96364	0.73579	0.26426	1.00556	0.73579	0.96	0.0838	475	

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2H4)^b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2)^b (H4)^c$$

Where: Y = component weight in pounds

D = tree d.b.h. in inches

$H4$ = treeheight to 4-inch top in feet

a' , a'' , b , c = regression coefficients

³log₁₀ form

Table 17. -- Regression equations for estimating cubic-foot volume of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and height to a 4-inch top as the independent variables

Species or species group	Volume wood & bark or wood only	Regression equation coefficients						Coefficient of determination (R^2)	Standard error ³ ($S_{y,x}$)	No. of trees sampled
		Trees < 11.0 inches d.b.h. ¹		Trees > 11.0 in d.b.h. ²						
		a'	b	a''	b	c				
TOTAL TREE										
Soft Hardwoods	Wd&Bk wood	0.05474 0.04134	0.70054 0.70969	0.01130 0.00937	1.02957 1.01925	0.70054 0.70969	0.94 0.99	0.0485 0.0535	128 128	
Basswood	Wd&Bk Wood	0.04080 0.02709	0.73184 0.75153	0.00749 0.00439	1.08521 1.13087	0.73184 0.75153	0.98 0.98	0.0565 0.0545	18 18	
Blackgum (upland)	Wd&Bk Wood	0.05331 0.03752	0.70720 0.71700	0.01657 0.01067	0.95079 0.97917	0.70720 0.71700	0.99 0.99	0.0497 0.0524	18 18	
Red maple	Wd&Bk Wood	0.04535 0.03424	0.73493 0.74945	0.01864 0.01656	0.92030 0.90088	0.73493 0.74945	0.98 0.98	0.0538 0.11530	30 30	
Yellow-poplar	Wd&Bk Wood	0.05378 0.04522	0.69692 0.69357	0.00918 0.00780	1.06554 1.05996	0.69692 0.69357	0.99 0.99	0.0367 0.0376	62 62	
Hard Hardwoods	Wd&Bk Wood	0.03974 0.02666	0.73923 0.76032	0.00750 0.00552	1.08690 1.08874	0.73923 0.76032	0.98 0.98	0.0595 0.0656	347 347	
White ash	Wd&Bk wood	0.04333 0.02863	0.72793 0.75098	0.01052 0.00760	1.02317 1.07761	0.72793 0.75098	0.97 0.97	0.0704 0.0709	52 52	
Sweet birch	Wd&Bk Wood	0.06728 0.05171	0.69628 0.70489	0.01934 0.01635	0.95624 0.94500	0.69628 0.70489	0.99 0.99	0.0333 0.0335	21 21	
Black locust	Wd&Bk Wood	0.03373 0.02223	0.75175 0.76526	0.01325 0.01066	0.94608 0.91850	0.75125 0.76526	0.98 0.99	0.0575 0.0522	18 18	
Hickory	Wd&Bk Wood	0.02357 0.01416	0.79863 0.83119	0.00527 0.00374	1.11100 1.10881	0.79863 0.83119	0.98 0.99	0.0637 0.0625	54 54	
Black oak	Wd&Bk Wood	0.02878 0.01803	0.76935 0.79928	0.00172 0.00402	1.35710 1.11227	0.76935 0.79928	0.99 0.99	0.0403 0.0416	27 27	
Chestnut oak	Wd&Bk Wood	0.02749 0.01788	0.77663 0.79366	0.00642 0.00434	1.07994 1.08868	0.77663 0.79366	0.98 0.99	0.0578 0.0834	51 51	
North. red oak	Wd&Bk Wood	0.03597 0.02777	0.75490 0.76524	13.00986 0.00811	1.07482 1.02199	0.75490 0.76524	0.99 0.99	0.0415 0.0411	71 71	
Scarlet oak	Wd&Bk wood	0.07180 0.04451	0.67727 0.70926	0.01056 0.00706	1.07687 1.09332	0.67727 0.70926	0.99 0.99	0.0444 0.0424	27 27	
White oak	Wd&Bk Wood	0.05516 0.04323	0.69940 0.70290	0.00486 0.00364	1.20595 1.21889	0.69940 0.70290	0.99 0.99	I.0453 0.0430	28 28	
All Species	Wd&Bk Wood	0.04521 0.03169	0.72360 0.74013	0.00823 0.00627	1.07891 1.07801	0.72360 0.74013	0.98 0.98	I.0578 0.0639	415 475	

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2H^4)^b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2)^b (H^4)^c$$

Where: Y = component volume in cubic feet

D = tree d.b.h. in inches

$H4$ = tree height to 4-inch top in feet

a' , a'' , b , c = regression coefficients

³log₁₀ form

Table 18.--Regression equations for estimating cubic-foot volume of the total-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and height to a 4-inch top as the independent variables

Species species group	Volume wood & bark wood only	Regression equation coefficients						Coefficient of determination (R ²)	Standard error ³ (S _{y-x})	No. of trees sampled		
		Trees < 11.0 in d.b.h. ¹			Trees > 11.0 in d.b.h. ²							
TOTAL STEM												
Soft Hardwoods	Wd&Bk Wood	0.03746 0.02856	rI. 72416 0. 73561	0.00871 f-J. 00764	1. 02837 1. 01048	0. 72416 0. 73561	0. 99 0. 99	0. 0414 0. 0470	128 128			
Basswood	Wd&Bk Wood	0. 03371 0. 02195	II. 73050 0. 75703	0.00778 0. 00460	1. 03617 1. 08296	0.73050 0. 75703	0. 99 0. 99	0. 0039 I-I. 035	18 18			
Blackgum (upland)	Wd&Bk wood	0. 02359 0. 01543	n. 77495 0. 79862	0.01177 0. 00846	0.91997 0. 92396	n. 77495 0. 79862	n. 99 0. 99	0. 0300 0. 0345	18 18			
Red maple	Wd&Bk Wood	0.04727 0. 03392	0.69759 0. 72326	11. 01567 0. 01472	0. 97844 0. 89732	C-J. 69759 n. 72326	0. 99 0. 99	0. 0390 0. 0383	30 30			
Yellow-poplar	Wd&Bk wood	0. 04350 0. 03834	0.71115 0. 70393	0.00936 0. 00802	1.03155 1. 03020	0. 71115 0. 70393	n. 99 0. 99	0. 0346 0. 0348	62 62			
Hard Hardwoods	Wd&Bk Wood	0. 03369 0. 02288	0. 73486 0. 75831	0. 01017 0. 00732	0. 98455 0. 99601	0. 73486 0. 75831	0. 99 0. 99	0. 0458 0. 0520	347 347			
White ash	Wd&Bk wood	0.04012 0. 02669	0.71050 0. 73667	0.00929 0. 00686	1. 01546 1. 01996	0.71050 0. 73667	0. 98 0. 98	0. 0593 0. 0616	52 52			
Sweet birch	Wd&Bk wood	0.04491 0. 03732	0.70572 0. 71290	0.01558 0. 01520	0.92643 0. 90017	0. 70572 0. 71290	0. 99 0. 99	0. 0331 0. 0351	21 21			
Black locust	Wd&Bk Wood	Cl.02878 0. 01809	0.74727 0. 77187	0. 00937 0. 00872	0. 98133 0. 92407	0. 74727 0. 77187	0. 97 0. 98	0. 0658 0. 0589	18 18			
Hickory	Wd&Bk Wood	0.02651 0. 01507	0.75977 0. 80356	0. 00766 0. 00526	1. 01864 1. 02305	0. 75977 n. 80356	0. 99 0. 99	0. 0499 0. 0513	54 54			
Black oak	Wd&Bk Wood	0. 02665 0. 01672	0. 76146 0. 79414	0.01062 0. 00794	n. 95328 0. 94946	0. 76146 0. 79414	0. 99 0. 99	0. 0243 0. 0268	27 27			
Chestnut oak	Wd&Bk Wood	0.02773 0. 01767	0.76059 n. 78732	0.01082 0. 00650	0. 95689 0. 99076	0. 76059 n. 78232	n. 99 0. 99	0. 0518 0. 0492	51 51			
North. red oak	Wd&Bk Wood	0.03440 0. 02670	0. 73586 0. 74844	0.01199 0. 00974	0.95561 U. 95868	0.73586 0. 74044	0.99 0.99	0.0311 0.0316	71 71			
Scarlet oak	Wd&Bk wood	0. 03592 0. 02446	0. 73107 0. 75654	0. 01253 0. 00873	0.95066 0. 97133	0. 73107 0. 75654	0. 99 0. 99	0. 0311 0. 0327	27 27			
White oak	Wd&Bk Wood	0.04510 0. 03659	0.70008 0. 70428	0.00958 0. 00703	1. 02305 1. 04835	0. 70008 0. 70428	0. 99 0. 99	0. 0418 (I. 0423)	28 28			
All Species	Wd&Bk Wood	0.03463 0. 02463	U. 73223 0. 75060	0.00992 0. 00750	0. 99296 0. 99852	0.73223 0. 75060	0. 99 0. 99	0.0451 0.0512	475 475			

¹Trees < 11.0 inches d.b.h.

$$Y = a'(D^2/H^4)^b$$

²Trees > 11.0 inches d.b.h.

$$Y = a''(D^2)^b (H^4)^c$$

Where: Y = component volume in cubic feet

D = tree d.b.h. in inches

H4 = tree height to 4-inch top in feet

a', a'', b, c = regression coefficients

³log₁₀ form

Table 19.-Regression **equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d. b. h. and saw-log merchantable height as the independent variables**

Species or species group	Weight green or dry	<u>Regression equation coefficients¹</u>			Coefficient of determination (R ²)	Standard error ² (S _{y,x})	No. of trees sampled
		a	b	c			
TOTAL-TREE WOOD AND BARK							
Soft Hardwoods	Green	4.05976	1.15137	0.11698	0.95	0.0556	64
	Dry	1.86603	1.19791	0.07544	0.94	0.0648	64
Yellow-poplar	Green	3.63549	1.15471	0.14090	0.96	0.0514	38
	Dry	1.31796	1.18011	0.18123	0.97	0.0518	38
Hard Hardwoods	Green	2.98611	1.20675	0.16314	0.90	0.0728	194
	Dry	2.50064	1.17013	0.12749	0.90	0.0708	194
White ash	Green	4.12121	1.24290	-0.04067	0.87	0.0738	22
	Dry	3.48126	1.21437	-0.06425	0.86	0.0762	22
Hickory	Green	4.34712	1.18669	0.11729	0.94	0.0540	33
	Dry	3.05128	1.15651	0.13495	0.93	0.0582	33
Black oak	Green	3.41609	1.23276	0.068411	0.97	0.0381	18
	Dry	2.73215	1.17562	0.06050	0.97	0.0386	18
Chestnut oak	Green	3.58371	1.05408	0.32267	0.93	0.0571	32
	Dry	2.48376	1.05737	0.28062	0.93	0.0575	32
North. red oak	Green	5.99037	1.10049	0.15495	0.96	0.0470	35
	Dry	3.46886	1.09854	-0.15107	0.95	0.0525	35
Scarlet oak	Green	4.53057	1.21071	0.04946	0.96	0.0489	18
	Dry	2.91232	1.19164	0.04318	0.95	0.0538	18
White oak	Green	2.35939	1.28245	0.14044	0.97	0.0430	19
	Dry	1.32111	1.26763	0.17245	0.97	0.0458	19
All Species	Green	3.35825	1.22626	0.09181	0.90	0.0754	258
	Dry	2.35086	1.24448	0.01370	0.86	0.0924	258

Continued

Table 19.--Regression equations for estimating green and dry weight of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d. h. h. and saw-log merchantable height as the independent variables--Continued

Species or species group	Weight green or dry	Regression equation coefficients ¹			Coefficient of determination (R ²)	Standard error ² (S _{y,x})	No. of trees sampled
		a	b	c			
TOTAL TREE WOOD							
Soft Hardwoods	Green	3. 24470	1.16033	0.11400	0. 94	0. 0593	64
	Dry	1. 37310	1. 20500	0. 09655	0. 92	0. 0731	64
Yellow-poplar	Green	2. 79150	1. 16660	0. 14325	0. 96	0.0553	38
	Dry	0. 99658	1. 19403	0. 18713	0. 96	0.0558	38
Hard Hardwoods	Green	2. 32731	1. 70508	0. 18321	0.90	0.0750	194
	Dry	2. 12789	1. 15769	11. 13923	0. 89	0. 0751	194
White ash	Green	3. 45613	1.24018	-0.03654	0.87	0. 0732	22
	Dry	2. 91578	1. 22271	-0. 06896	0. 85	0. 7600	22
Hickory	Green	3. 26847	1. 15941	0. 18233	n. 94	0.0572	33
	Dry	2. 44480	1. 13369	0. 18065	0. 92	0. 0637	33
Black oak	Green	3. 11513	1. 20511	0.08186	0. 97	0.0419	18
	Dry	3. 37766	1. 10757	0. 04619	0. 96	0. 0435	18
Chestnut oak	Green	2.49920	1.05608	0.35718	0. 93	0. 0564	32
	Dry	1. 72630	1. 05331	IT. 32219	0. 93	0.0590	32
North. red oak	Green	4. 98757	1. 09466	0. 16954	0. 96	0. 0473	35
	Dry	2. 97391	1. 08462	0. 16492	0. 95	0. 0519	35
Scarlet oak	Green	3. 73344	1. 21738	0. 04638	0. 96	0. 0514	18
	Dry	2. 60260	1. 19230	0. 02328	0. 94	0. 0580	18
White oak	Green	1. 66906	1. 29182	0. 17117	0. 97	0.0468	19
	Dry	0. 93583	1. 27017	0. 21334	0. 96	0. 0507	19
All Species	Green	2. 65966	1. 22734	0. 10322	0. 90	0. 0780	258
	Dry	1. 90465	1. 23786	0. 02986	0. 84	0. 0969	258

¹Y = a(D²)^b (Mh)^c

Where: Y = component weight in pounds

D = tree d. h. h. in inches

Mh = tree saw-log merchantable height in feet

a,b,c = regression coefficients

²log₁₀ form

Table 20.--Regression equations for estimating green and dry weight of the saw-loy merchantable stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and saw-loy merchantable height as the independent variables

Species or species group	Weight green or dry	Regression equation coefficients ¹			Coefficient of determination (R^2)	Standard error ² (S_{y-x})	No. of trees sampled
		a	b	c			
SAW-LOG STEM WOOD AND BARK							
Soft Hardwoods	Green	rl. 55968	0. 97608	0. 76439	0.98	0.0394	64
	Dry	0.24291	1. 03375	0. 72406	0.97	0.0531	64
Yellow-poc ar	Green	0.68901	1.06155	0. 59776	0.98	0.0388	38
	Dry	0. 23686	1. 10009	0. 63576	0.98	0.0399	38
Hard Hardwoods	Green	0. 42639	1.04226	0. 78699	0.96	0.0529	194
	Dry	0. 38048	0. 99659	0. 74397	0.96	0.0468	194
White ash	Green	0. 37684	1.09124	0. 68547	0.97	0.0449	22
	Dry	0. 31732	1.06878	0. 65457	0.96	0.0494	22
Hickory	Green	0. 58322	1. 00433	0. 76511	0.91	0.0303	33
	Dry	0. 42405	0.96934	0. 77888	0.98	0.0328	33
Black oak	Green	0. 49216	1. 04351	0. 74573	0.99	0.0145	18
	Dry	0. 46869	0.95839	0. 72629	0.98	0.0228	18
Chestnut oak	Green	0. 63082	0. 95792	0.80829	0.98	0.0342	32
	Dry	0. 45925	0.95093	0. 94403	0.98	0.0344	32
North. red oak	Green	0. 76656	0. 99153	0.72285	0.98	0.0324	35
	Dry	0. 43066	0. 99038	II. 71939	0.98	0.0374	35
Scarlet oak	Green	0.69724	0. 96281	0. 78401	0.99	0.0250	18
	Dry	0. 45295	0. 92838	0.78994	0.98	0.0286	18
White oak	Green	0. 49208	1. 08126	0. 70438	0.93	0.0601	19
	Dry	0. 27107	1. 05723	0. 74927	0.94	0.0562	19
All Species	Green	0. 47048	1.06146	0. 72104	0.95	0.0593	258
	Dry	0. 33634	1.07137	0. 64708	0.92	0.0762	258

Continued

Table 20.--Regression equations for estimating green and dry weight of the saw-log merchantable stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d. h. h. and saw-log merchantable height as the independent variables--Continued

Species or species group	Weight green or dry	Regression equation coefficients ¹			Coefficient of determination (R ²)	Standard error ² (S _{y,x})	No. of trees sampled
		a	b	c			
SAW LOG STEM WOOD							
Soft Hardwoods	Green	0.50293	0.99146	0.73096	0.98	0.0450	64
	Dry	0.20254	1.04938	0.70802	0.96	0.0621	64
Yellow-poplar	Green	0.55389	1.08099	0.58465	0.98	0.0430	38
	Dry	0.18726	1.12510	0.61962	0.98	0.0453	38
Hard Hardwoods	Green	0.35194	1.04701	1.79339	0.96	0.0538	194
	Dry	0.33381	0.99188	n.74595	0.96	0.0493	194
White ash	Green	0.34623	1.08809	0.67732	n.96	0.0470	22
	Dry	0.28903	1.07233	0.64416	0.95	0.0511	22
Hickory	Green	0.46205	0.99 169	0.80794	0.99	0.0312	33
	Dry	0.34990	0.95888	0.80950	0.98	0.0366	33
Black oak	Green	0.47034	1.02642	0.74214	0.99	0.0207	18
	Dry	0.57210	0.90650	0.70112	0.97	0.0273	18
Chestnut oak	Green	0.43231	0.47235	0.84074	0.98	0.0367	32
	Dry	0.30374	0.9625X	0.80876	0.97	0.0391	32
North. red oak	Green	0.66689	0.99419	0.72204	0.98	0.0332	35
	Dry	0.37474	0.98637	0.72305	0.98	0.0377	35
Scarlet oak	Green	0.60720	0.97327	0.77023	0.99	0.0261	18
	Dry	0.41128	0.93365	0.76718	0.98	0.0304	18
White oak	Green	0.37821	1.08957	0.72864	0.93	0.0618	19
	Dry	0.20442	1.05844	0.78758	0.93	0.0587	19
All Species	Green	0.40454	1.06936	0.71126	0.95	0.0619	258
	Dry	0.29232	1.07303	0.64172	0.91	0.0803	258

¹Y = a(D²)b(Mh)c

Where: Y = component weight in pounds

D = tree d. h. h. in inches

Mh = tree saw-log merchantable height in feet

a,b,c = regression coefficients

²log₁₀ form

Table 21 . . . Regression equations for estimating cubic-foot volume of the above-stump total-tree wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d. h. h. and saw-log merchantable height as the independent variables

Species or species group	Volume wood & bark or wood only	Regression equation coefficients'			Coefficient of determination (R ²)	Standard error ² (S _{y,x})	No. of trees sampled
		a	b	c			
TOTAL TREE							
Soft Hardwoods	Wd&Bk Wood	0.06348 0.05071	1.15377 1.17519	0.16627 0.14027	0.96 0.95	0.0542 0.0593	64 64
Yellow poplar	Wd&Bk Wood	0.05911 0.04603	1.09737 1.11422	0.26467 0.25069	0.98 0.97	0.0424 0.0466	38 38
Hard Hardwoods	Wd&Bk Wood	0.06694 0.04642	1.17704 1.19770	0.12273 0.13386	0.93 n.92	0.0574 0.0637	194 194
White ash	Wd&Bk Wood	0.06137 0.04236	1.27971 1.26906	0.05813 0.04386	0.91 0.91	0.0628 0.0630	22 22
Hickory	Wd&Bk wood	0.07906 0.05522	1.71638 1.19934	0.04475 0.10844	n.95 0.94	0.0526 0.0539	33 33
Black oak	Wd&Bk Wood	0.04500 0.04156	1.24048 1.21387	0.11235 0.11566	0.98 0.97	0.0345 0.11379	18 18
Chestnut oak	Wd&Bk Wood	0.07369 0.04431	1.05046 1.05971	0.26836 0.31747	0.95 0.95	0.0496 0.0493	32 32
North. red oak	Wd&Bk Wood	0.09386 0.07549	1.09528 1.09058	0.15845 0.17826	0.96 0.96	0.0465 0.0469	35 35
Searlet oak	Wd&Bk Wood	0.06083 0.04770	1.23182 1.24873	0.05781 0.05083	0.96 0.96	0.0475 0.0491	18 18
White oak	Wd&Bk Wood	0.04580 0.03026	1.26747 1.29052	0.10850 0.13024	0.97 0.97	0.0390 0.0414	19 19
All Species	Wd&Bk Wood	0.06486 0.04764	1.17578 1.19441	0.13215 (1.13107)	0.94 0.93	0.0565 0.0623	258 258

'Y = a(D²)^b(Mh)^c

Where: Y = component volume in cubic feet
D = tree d.h.h. in inches
Mh = saw-log merchantable height in feet
a,b,c = regression coefficients

2log₁₀ form

Table 22. . . Regression equations for estimating cubic-foot volume of the saw-log merchantable-stem wood and bark combined and wood alone for hardwood species in the Southern Appalachian Mountains, with d.b.h. and saw-log merchantable height as the independent variables

Species or species group	Volume wood & bark or wood only	Regression equation coefficients ¹			Coefficient of determination (R ²)	Standard No. of error ² (S _{y,x}) trees sampled
		a	b	c		
SAW LOG STEM						
Soft Hardwoods	WLRBk Wood	0.00780 0.00701	0.99177 1.02126	0.82682 0.76649	0.99 0.99	0.0330 0.0348 64 64
Yellow-poplar	WLRBk Wood	0.01052 0.00841	1.01910 1.04599	0.72073 0.69141	0.99 0.99	0.0283 0.0320 38 38
Hard Hardwoods	WLRBk Wood	0.00967 0.00722	1.01633 1.04258	0.73612 0.73139	0.98 0.97	0.0378 0.0408 194 194
White ash	WLRBk Wood	0.00507 0.00393	1.10571 1.13881	0.77375 0.74777	0.97 0.97	0.0407 0.0425 22 22
Hickory	Wd&Bk Wood	0.01177 0.00910	1.03084 1.02807	0.66606 0.69683	0.98 n. 98	0.0348 0.0337 33 33
Black oak	WLRBk Wood	0.130640 0.00616	1.05525 1.03754	0.78692 0.77832	0.99 n. 99	0.0189 0.0214 18 18
Chestnut oak	Wd&Bk Wood	0.01297 0.00758	0.95130 0.97846	n. 75417 n. 79829	n. 97 0.97	0.0389 0.0375 32 32
North. red oak	WLRBk Wood	0.01156 0.00983	0.99620 1.00126	0.71988 0.72005	0.98 0.98	0.0331 0.0337 35 35
-Scarlet oak	Wd&Bk Wood	0.00922 0.00770	n. 98666 1.00493	0.79196 0.77708	n. 99 0.99	0.0247 0.0265 18 18
White oak	WLRBk wood	0.00959 0.00723	1.07178 1.09265	0.66050 0.66626	n. 93 0.93	0.0578 0.0578 19 19
All Species	Wd&Bk Wood	0.00876 0.00707	1.01407 1.04112	0.76589 0.73845	0.98 0.98	0.0370 0.0394 258 258

¹Y = a(D²)^b(Mh)^c

Where: Y = component volume in cubic feet
D = tree d.b.h. in inches
Mh = saw-log merchantable height in feet
a,b,c = regression coefficients

²log₁₀ form

Table 23.--Regression coefficients for estimating above-stump stem weight to a specified d.o.b. top diameter as a proportion of the total-stem weight for hardwood species in the Southern Appalachian Mountains

Species	Regression equation and coefficients ¹						
	Green weight			Dry weight			$\gamma_R = e^a(d)^b(D)^c$
	a	b	c	a	b	c	
WOOD AND BARK							
Soft Hardwoods	-2.21340	3.69663	-4.00734	-2.32156	3.64529	-3.97653	
<i>basswood</i>	-1.29361	3.91861)	-4.02401	-1.28273	3.87891	-3.97979	
Blackgum (upland)	-1.67063	4.31740	-4.55837	-1.62090	4.27337	-4.51105	
<i>Red maple</i>	-1.48733	4.07172	-4.15788	-1.43083	4.05497	-4.12303	
<i>Yellow-poplar</i>	-3.13237	3.24562	-3.77925	-3.54839	3.17747	-3.76535	
Hard Hardwoods	-2.16093	3.80095	-4.16788	-7.16635	3.76999	-4.13510	
<i>White ash</i>	-0.85286	3.25306	-3.30904	-0.84279	3.28603	-3.33279	
<i>Sweet birch</i>	-0.86248	4.24300	-4.12996	-0.81251	4.21844	-4.08482	
<i>Black locust</i>	-1.47964	3.34777	-3.5577')	-1.27900	3.33578	-3.49181	
<i>Hickory</i>	-4.46031	3.84056	-4.44415	-4.48018	3.83474	-4.43554	
<i>Black oak</i>	-4.21018	3.91449	-4.53686	-4.35164	3.85984	-4.49173	
<i>Chestnut oak</i>	-2.33213	4.00430	-4.37862	-7.25664	4.00092	-4.35574	
<i>North. red oak</i>	-1.78853	4.05675	-4.35269	-1.90345	3.95736	-4.27185	
<i>Scarlet oak</i>	-2.56711	3.67657	-4.17429	-2.65117	3.58558	-4.09877	
<i>White oak</i>	-12.89794	2.66329	-4.01784	-12.00001	2.64614	-3.96330	
All Species	-2.18145	3.83824	-4.18924	-2.19443	3.79947	-4.15151	
WOOD ONLY							
Soft Hardwoods	-2.14922	3.76998	-4.07255	-2.24102	3.72688	-4.04629	
<i>Hasswood</i>	-1.09439	4.07301	-4.11466	-1.05926	4.01311	-4.04160	
Blackgum (upland)	-1.45781	4.43140	-4.61952	-1.34282	4.39292	-4.56007	
<i>Red maple</i>	-1.37214	4.19926	-4.25422	-1.33864	4.16262	-4.20601	
<i>Yellow-poplar</i>	-3.16748	3.28202	-3.82586	-3.51229	3.24724	-3.83278	
Hard Hardwoods	-2.00963	3.93252	-4.27051	-2.05785	3.87551	-4.22144	
<i>White ash</i>	-0.79212	3.40027	-3.42870	-0.80589	3.38150	-3.41391	
<i>Sweet birch</i>	-0.76917	4.34999	-4.19013	-0.72051	4.31785	-4.13646	
<i>Black locust</i>	-1.42866	3.44696	-3.65524	-1.27952	3.42285	-3.58019	
<i>Hickory</i>	-4.23466	3.96634	-4.54756	-4.36489	3.93623	-4.52542	
<i>Black oak</i>	-3.74181	4.01847	-4.591125	-3.94567	3.93141	-4.53034	
<i>Chestnut oak</i>	-2.23141	4.17046	-4.53052	-2.22131	4.14820	-4.50149	
<i>North. red oak</i>	-1.64068	4.17440	-4.43072	-1.76424	4.05667	-4.34109	
<i>Scarlet oak</i>	-2.34160	3.76911	-4.27934	-2.49044	3.64618	-4.13747	
<i>White oak</i>	-13.82341	2.74531	-4.14893	-12.83857	2.72014	-4.08425	
All Species	-2.03248	3.95927	-4.28299	-2.06850	3.90215	-4.23251	

' Where: γ_R = stem weight to top d.o.b./total-stem weight ratio

d = stem specified top d.o.b. in inches

D = tree diameter at hrcast height in inches

a,b,c = regression coefficients

e = 2.71828 (base of log E)

Table 24...Regression coefficients for estimating above-stump stem volume to a specified d.o.b. top diameter as a proportion of the total-stem volume for hardwood species in the Southern Appalachian Mountains

Species	Regression equation and coefficients'					
	Wood and bark			Wood only		
	a	b	c	a	b	c
Soft Hardwoods						
Basswood	-2.65041	3.63613	-4.02198	-2.49527	3.75217	-4.11106
Blackgum (upland)	-1.57495	3.83251	-4.01512	-1.44150	3.94456	-4.09578
Red maple	-3.11888	4.50575	-4.98933	-3.00702	4.60007	-5.08323
Yellow poplar	-1.64317	3.97988	-4.10493	-1.56405	4.07950	-4.18514
Hard Hardwoods						
White ash	-2.11609	3.69565	-4.06590	-2.01927	3.85912	-4.20784
Sweet birch	-0.83488	3.28203	-3.33403	-0.81118	3.41128	-3.45707
Black locust	-0.54868	4.13144	-3.86409	-0.47153	4.25228	-3.92355
Hickory	-1.33357	3.33736	-3.51539	-1.72747	3.92136	-4.14425
Black oak	-4.24857	3.92307	-4.55072	-3.86927	4.03853	-4.63239
Chestnut oak	-1.89796	3.77009	-4.07300	-1.81088	3.92867	-4.21943
North. red oak	-2.08619	3.93878	-4.30635	-1.97257	4.04188	-4.38210
Scarlet oak	-2.72820	3.63031	-4.15933	-2.77208	3.93948	-4.44871
White oak	-13.81307	2.63083	-4.00315	-14.82177	2.71406	-4.13623
All Species	-2.29927	3.76224	-4.14072	-2.18185	3.90966	-4.26572

' Where: Y_R = stem volume to top d.o.b./total-stem volume ratio

d = stem specified top d.o.b. in inches

D = tree diameter at breast height in inches

a, b, c = regression coefficients

e = 2.71828 (base of log E)

Table 25.--Regression coefficients for estimating stem weight to a specified d.o.b. top diameter as a proportion of the saw-log stem weight for hardwood species in the Southern Appalachian Mountains

Species	Ratio equation and coefficients ^a					
	Green weight			Dry weight		
	a	b	c	a	b	c
WOOD AND BARK						
Soft Hardwoods	20. 03667	-1.15011	0.30738	22.65502	-1.17892	0.30687
Yellow-poplar	10. 22822	-0.98536	0. 36914	13. 88862	-1. 05701	0.35508
Hard Hardwoods	21.83094	-1.20030	0. 34703	22. 05487	-1.19924	0.35256
White ash	7.59795	-0. 84256	0. 34097	9. 74167	-0. 91132	0.33776
Hickory	5.62084	-0. 78282	0.33669	6. 31538	-0.81008	0.34761
Black oak	8.59159	-0. 96498	0. 34859	Tn. 22071	-1. 00848	0.36275
Chestnut oak	10.16324	-1.02615	0. 34438	11.77550	-1.06016	0.35889
North. red oak	11.43588	-1.07021	0.33698	12. 89204	-1.09324	0.35282
Scarlet oak	13.89580	-1.14183	0. 33685	16. 33739	-1.18006	0.35211
White oak	9.77724	-1.03753	0.24075	11. 57127	-1.07768	0.24979
All Species	22.10956	-1.19842	0.33093	23. 34055	-1.20928	0.33401
WOOD ONLY						
Soft Hardwoods	19. 97709	-1. 15553	0.30428	22. 66578	-1.18538	0.30423
Yellow-poplar	9. 93078	-0. 98459	0.36906	13. 76196	-1.06203	0.35548
Hard Hardwoods	22. 56773	-1. 21533	0.34214	21. 93139	-1.20369	0.34479
White ash	7. 64692	-0.85097	0. 33715	9. 74786	-0.91666	n. 33500
Black oak	8. 45354	-0. 96445	0. 34659	8. 46965	-0.96165	n. 34694
Hickory	5.58002	-0.78519	n. 33356	5. 64166	-0.78507	n.33487
Chestnut oak	10.71803	-1.05121	n. 33926	10.71403	-1.04734	0.34011
North. red oak	11.20075	-1.06846	0. 33485	10.98689	-1.05719	0.33593
Scarlet oak	13.44225	-1.13557	0.33509	13. 58787	-1.13547	0.33509
White oak	9.93996	-1.04879	0. 24099	9. 78499	-1.03963	0.24026
All Species	22. 54655	-1. 20977	0.32670	23. 73192	-1.21400	0.32807

Y_R = ratio of stem weight or volume to top d.o.b. to saw-log stem

Mh = saw-log merchantable height in feet

d = specified top diameter in inches

D = tree diameter at breast height in inches

.78 = constant based on average form class

a, b, c = regression coefficients

e = base of natural log

Table 26.--Regression coefficients for estimating stem volume to a specified d.o.b. top diameter as a proportion of the saw-log stem volume for hardwood species in the Southern Appalachian Mountains

Species	Ratio equation and coefficients ^a					
	Wood and bark			Wood only		
	a	b	c	a	b	c
Soft Hardwoods	17. 02169	-1. 10696	0. 30429	16. 72438	-1. 10825	0. 30068
Yellow poplar	9. 53972	-0. 97107	n. 36947	9. 08017	-0. 96511	0. 36804
Hard Hardwoods	18. 34030	-1. 15240	0. 34627	18. 69832	-1. 16454	0. 34023
White ash	6. 19949	-0. 78674	0. 33896	6. 14057	-0. 79208	0. 33351
Hickory	4. 46875	-0. 72269	0. 33443	4. 25711	-0. 71497	0. 33028
Black oak	7. 13860	-0. 91520	0. 34770	6. 68841	-0. 90165	0. 34567
Chestnut oak	7. 98372	-0. 95562	0. 34672	8. 18125	-0. 97506	0. 34032
North. red oak	9. 70538	-1. 02782	0. 33574	9. 06390	-1. 01358	0. 33344
Scarlet oak	12. 08963	-1. 10806	0. 33484	11. 17720	-1. 09039	0. 33229
White oak	8. 12968	-0. 98631	0. 23765	7. 84004	-0. 98376	0. 23730
All Species	18. 67262	-1. 15229	0. 32937	18. 84524	-1. 16148	0. 37498

Y_R = ratio of stem weight or volume to top d.o.b. to saw-log stem

Mh = saw-log merchantable height in feet

d = specified top diameter in inches

D = tree diameter at breast height in inches

.78 = constant based on average form class

a,b,c = regression coefficients

e = base of natural log



Clark, Alexander, III; Schroeder, James G.

Weight, volume, and physical properties of major hardwood species in the Southern Appalachian Mountains. Res. Pap. SE-253. Asheville, NC: U.S. Department of Agriculture, Forest Service, Southeastern Forest Experiment Station; 1985. 63 pp.

The weight, volume, and physical properties of trees 1 to 20 inches d.b.h. were determined for basswood, blackgum (upland), red maple, yellow-poplar, white oak, sweet birch, black locust, hickory, black oak, chestnut oak, northern red oak, scarlet oak, and white oak in the Southern Appalachian Mountains. Hard hardwoods, soft hardwoods, and individual species equations are presented for predicting green and dry weight and green volume of the total tree above-stump and its components by using d.b.h. and total height, d.b.h. and height to a 4-inch top, d.b.h. and saw-log merchantable height, and d.b.h. alone. Average specific gravity, moisture content, and weight per cubic foot of wood, bark, and wood and bark combined are presented for each species by tree size class and component. Bark percentage is also presented for each species by tree size class and component.

Keywords: Biomass, equations, specific gravity, moisture content, bark percentage, weight per cubic foot.

Clark, Alexander, III; Schroeder, James G.

Weight, volume, and physical properties of major hardwood species in the Southern Appalachian Mountains. Res. Pap. SE-253. Asheville, NC: U.S. Department of Agriculture, Forest Service, Southeastern Forest Experiment Station; 1985. 63 pp.

The weight, volume, and physical properties of trees 1 to 20 inches d.b.h. were determined for basswood, blackgum (upland), red maple, yellow-poplar, white oak, sweet birch, black locust, hickory, black oak, chestnut oak, northern red oak, scarlet pak, and white oak in the Southern Appalachian Mountains. Hard hardwoods, soft hardwoods, and individual species equations are presented for predicting green and dry weight and green volume of the total tree above-stump and its components by using d.b.h. and total height, d.b.h. and height to a 4-inch top, d.b.n. and saw-log merchantable height, and d.b.h. alone. Average specific gravity, moisture content, and weight per cubic foot of wood, bark, and wood and bark combined are presented for each species by tree size class and component. Bark percentage is also presented for each species by tree size class and component.

Keywords: Biomass, equations, specific gravity, moisture content, bark percentage, weight per cubic foot.





The Forest Service, U.S. Department of Agriculture, is dedicated to the principle of multiple use management of the Nation's forest resources for sustained yields of wood, water, forage, wildlife, and recreation. Through forestry research, cooperation with the States and private forest owners, and management of the National Forests and National Grasslands, it strives—as directed by Congress—to provide increasingly greater service to a growing Nation.

CJSDA policy does not permit discrimination because of race, color, national origin, sex or religion. Any person who believes he or she has been discriminated against in any USDA-related activity should write immediately to the Secretary of Agriculture, Washington, D.C. 20250.